

Advanced $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ Z-Scheme Multi-Heterojunction Photocatalyst for Efficient Solar Energy Conversion, CO_2 Reduction, Hydrogen Evolution and Environmental Remediation

Binyamin Siddiqui¹, Muhammad Abid Sultani², Talha Javed³, Muhammad Azam Shani⁴, Muhammad Haris⁵, Ehtasham Ul Haq⁶, Sahrish Younus⁷

¹Department of Chemistry, Bacha Khan University Charsadda, Pakistan

²Department of Physics, University of Agriculture Faisalabad, Faisalabad, Pakistan

³Catalysis and Sensing Materials Lab, Department of Physics, Comsats University Islamabad, Islamabad Campus, Pakistan

⁴Department of Physics, Riphah International University, Pakistan

⁵Department of Materials National Textile University Faisalabad 37610 Pakistan

⁶Center of Excellence in Solid State Physics, University of the Punjab, Lahore

⁷Department of Chemistry, University of Agriculture Faisalabad, Faisalabad, Pakistan

DOI: <https://doi.org/10.36348/sjls.2026.v11i08.010>

| Received: 21.06.2026 | Accepted: 05.08.2026 | Published: 25.08.2026

*Corresponding author: Binyamin Siddiqui

Department of Chemistry, Bacha Khan University Charsadda, Pakistan

Abstract

The development of multifunctional photocatalysts capable of simultaneously addressing solar energy conversion, carbon-neutral fuel production, and environmental remediation remains a significant challenge due to rapid charge carrier recombination and limited visible-light utilization. In this study, a novel $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ Z-scheme multi-heterojunction photocatalyst was successfully synthesized via a combination of hydrothermal and in situ deposition methods to achieve highly efficient solar-driven photocatalytic performance. Structural, morphological, and spectroscopic characterizations confirmed the successful construction of a tightly integrated multi-heterojunction with intimate interfacial contact among all constituent phases. The engineered Z-scheme architecture significantly enhanced visible-light harvesting, facilitated rapid spatial separation of photogenerated charge carriers, and suppressed electron-hole recombination. Electrochemical analyses further verified reduced charge-transfer resistance and improved interfacial charge transport. Under simulated solar irradiation, the optimized photocatalyst exhibited outstanding photocatalytic performance, achieving hydrogen evolution at a rate of $2138 \mu\text{mol h}^{-1} \text{g}^{-1}$, while CO_2 photoreduction generated CO ($18 \mu\text{mol g}^{-1} \text{h}^{-1}$) and CH_4 ($16 \mu\text{mol g}^{-1} \text{h}^{-1}$) as the major solar fuels. Simultaneously, the composite demonstrated 98.4% degradation of representative organic pollutants with 86.7% mineralization efficiency, highlighting its excellent capability for wastewater purification. Radical trapping experiments and band structure analysis revealed that photogenerated electrons together with $\cdot\text{OH}$ and $\cdot\text{O}_2^-$ radicals were the dominant reactive species governing the enhanced photocatalytic activity. The superior performance was attributed to the synergistic interaction of CoFe_2O_4 , BiVO_4 , Bi_2WO_6 , and $\text{g-C}_3\text{N}_4$, which provided broad-spectrum solar absorption, abundant active sites, enhanced redox capability, and efficient charge migration through the direct Z-scheme pathway. Furthermore, the photocatalyst retained 94.6% of its initial activity after five consecutive photocatalytic cycles, confirming its excellent structural stability and long-term durability. This work presents an effective strategy for designing advanced Z-scheme multi-heterojunction photocatalysts that integrate solar energy conversion, CO_2 utilization, hydrogen production, and environmental remediation within a single high-performance platform, offering considerable potential for sustainable energy and environmental applications.

Keywords: Z-scheme photocatalyst; CoFe_2O_4 ; CO_2 photoreduction; Hydrogen evolution; Environmental remediation; Solar energy conversion.

Copyright © 2026 The Author(s): This is an open-access article distributed under the terms of the Creative Commons Attribution 4.0 International License (CC BY-NC 4.0) which permits unrestricted use, distribution, and reproduction in any medium for non-commercial use provided the original author and source are credited.

INTRODUCTION

The increasing demand for sustainable energy and the urgent need to mitigate environmental pollution

Citation: Siddiqui, B., Sultani, M. A., Javed, T., Shani, M. A., Haris, M., Ul Haq, E., & Younus, S. (2026). Advanced $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ Z-Scheme Multi-Heterojunction Photocatalyst for Efficient Solar Energy Conversion, CO_2 Reduction, Hydrogen Evolution and Environmental Remediation. *Haya Saudi J Life Sci*, 11(8), 507-536. <https://doi.org/10.36348/sjls.2026.v11i08.010>

have stimulated extensive research into advanced photocatalytic materials capable of utilizing solar energy for multiple applications. Semiconductor photocatalysis has emerged as an attractive technology because it simultaneously enables renewable hydrogen production, photocatalytic CO₂ conversion, and degradation of hazardous organic pollutants under mild reaction conditions [1,2]. Despite substantial progress, the practical efficiency of conventional photocatalysts remains limited by inadequate visible-light absorption, rapid recombination of photogenerated charge carriers, and insufficient redox capability. These challenges have accelerated the development of advanced heterojunction photocatalysts, particularly direct Z-scheme architectures, which offer efficient charge separation while preserving strong oxidation and reduction potentials. In this context, the rational integration of CoFe₂O₄, BiVO₄, Bi₂WO₆, and g-C₃N₄ into a multifunctional Z-scheme heterostructure represents a promising strategy for achieving efficient solar energy conversion, hydrogen evolution, CO₂ photoreduction, and environmental remediation [3]. Accordingly, this introduction first discusses the global energy and environmental challenges, followed by the fundamentals of semiconductor photocatalysis, recent advances in heterojunction engineering, the advantages of direct Z-scheme systems, the selection of constituent materials, the existing research gap, and the novelty and objectives of the present study [4,5,6,7,8].

Global Energy and Environmental Challenges

The rapid growth of industrialization, urban expansion, and global energy consumption has intensified concerns regarding fossil fuel depletion and environmental degradation. The continuous dependence on coal, petroleum, and natural gas has substantially increased greenhouse gas emissions, accelerating global warming and climate change. Carbon dioxide (CO₂), the dominant anthropogenic greenhouse gas, has reached unprecedented atmospheric concentrations and is recognized as a primary contributor to rising global temperatures and extreme weather events. At the same time, the discharge of hazardous organic contaminants from industrial, pharmaceutical, textile, and agricultural activities has severely affected water resources and ecosystem health [9,10,12]. Conventional treatment technologies often require high energy input, generate secondary pollutants, or exhibit limited efficiency toward persistent contaminants. Consequently, developing sustainable technologies capable of simultaneously addressing energy shortages and environmental pollution has become an important scientific priority. Among various renewable energy sources, solar energy is considered one of the most abundant, clean, and sustainable resources available on Earth. Recent research has increasingly focused on integrated technologies that combine renewable energy production with environmental remediation. Such multifunctional systems are capable of converting solar energy into valuable fuels while simultaneously

removing toxic pollutants from water and air. This dual functionality not only improves energy utilization but also supports sustainable environmental management. Consequently, photocatalytic materials have attracted considerable attention as promising candidates for next-generation clean energy and environmental applications [13,14,18].

Solar Photocatalysis as a Sustainable Solution

Semiconductor photocatalysis has emerged as one of the most promising approaches for utilizing solar energy to drive environmentally beneficial chemical reactions under mild operating conditions. Since the pioneering discovery of photocatalytic water splitting, extensive research has been devoted to designing semiconductor materials capable of converting sunlight into chemical fuels. In addition to hydrogen generation, photocatalysis has demonstrated significant potential for CO₂ conversion, degradation of hazardous organic pollutants, antibacterial treatment, nitrogen fixation, and self-cleaning applications. These diverse applications highlight the versatility of photocatalytic technology in addressing multiple global challenges through a single sustainable platform [15,16,17,18].

Despite these advantages, the practical implementation of photocatalysis is still limited by several intrinsic challenges associated with conventional semiconductor materials. Most photocatalysts exhibit insufficient visible-light absorption, rapid recombination of photogenerated charge carriers, and inadequate surface reaction kinetics, resulting in relatively low quantum efficiency. Consequently, current research has shifted toward developing advanced heterostructured photocatalysts capable of maximizing solar energy utilization while maintaining high photocatalytic activity and long-term stability [19-24].

Fundamentals of Semiconductor Photocatalysis

The photocatalytic process begins when a semiconductor absorbs photons possessing energy equal to or greater than its band-gap energy. This excitation promotes electrons from the valence band to the conduction band, leaving positively charged holes in the valence band. The generated electrons and holes migrate toward the catalyst surface, where they participate in reduction and oxidation reactions with adsorbed reactants. Conduction-band electrons reduce electron acceptors such as CO₂ or protons to produce solar fuels, whereas valence-band holes oxidize water or hydroxide ions to generate highly reactive oxygen species capable of decomposing organic pollutants [25-29].

In recent years, significant progress has been made through band-gap engineering, defect regulation, morphology control, cocatalyst loading, and heterojunction construction. Among these approaches, heterojunction engineering has demonstrated exceptional potential because it simultaneously enhances

light absorption, promotes charge separation, and improves interfacial electron transfer. These advantages have established heterostructured photocatalysts as one of the most effective strategies for designing highly efficient solar-driven photocatalytic systems. Consequently, considerable attention has been directed toward constructing advanced multi-component Z-scheme photocatalysts capable of integrating hydrogen evolution, CO₂ reduction, and environmental remediation within a single multifunctional platform [30-33].

Limitations of Single Semiconductor Photocatalysts

Although numerous semiconductor photocatalysts have been investigated for solar energy conversion and environmental remediation, the performance of single-component materials remains unsatisfactory for practical applications. Most conventional photocatalysts suffer from rapid recombination of photogenerated electron-hole pairs,

which significantly reduces quantum efficiency and limits photocatalytic activity. In addition, many semiconductors possess either a wide band gap or inappropriate band-edge positions, restricting visible-light absorption and decreasing solar energy utilization.

Advantages of Heterojunction Engineering

Heterojunction engineering has emerged as one of the most effective strategies for overcoming the intrinsic drawbacks of single semiconductor photocatalysts. The integration of two or more semiconductors with complementary electronic structures creates an internal interface that promotes directional charge transfer and suppresses electron-hole recombination. Consequently, more photogenerated charge carriers remain available for surface redox reactions. The presence of multiple charge-transfer pathways also contributes to improved catalytic performance under visible-light irradiation [34-39].

Table 1: Comparison of Representative Visible-Light Photocatalysts Reported in Recent Literature

Photocatalyst	Synthesis	Main Application	Key Performance	Stability
g-C ₃ N ₄ /Bi ₂ WO ₆	Hydrothermal	Tetracycline degradation	88.03% degradation (120 min)	81.01% after 5 cycles
Bi ₂ WO ₆ /g-C ₃ N ₄ (S-scheme)	Hydrothermal	CO ₂ reduction	CH ₄ : 18.90 μmol g ⁻¹ h ⁻¹ ; CO: 17.78 μmol g ⁻¹ h ⁻¹	93% after 8 cycles
BiVO ₄ /g-C ₃ N ₄	Hydrothermal	RhB degradation	~100% degradation (60 min)	High stability
BiVO ₄ -Bi ₂ WO ₆ /g-C ₃ N ₄	Hydrothermal	RhB & TC degradation	96.7% (RhB); 94.8% (TC)	Stable recycling
BiOI/g-C ₃ N ₄ /Bi ₂ WO ₆ (Double Z-scheme)	Hydrothermal	RhB degradation	100% degradation (30 min)	Stable after 5 cycles
Sr-BiVO ₄ /g-C ₃ N ₄	Hydrothermal-assisted	Dye degradation	Reduced band gap to 2.17 eV; enhanced solar-light activity	Good stability
CoFe ₂ O ₄ /BiVO ₄ /Bi ₂ WO ₆ /g-C ₃ N ₄ (This Work)	In-situ hydrothermal	H ₂ production + CO ₂ reduction + Pollutant degradation	94–98% dye degradation; H ₂ evolution	Stable after 4–5 cycles

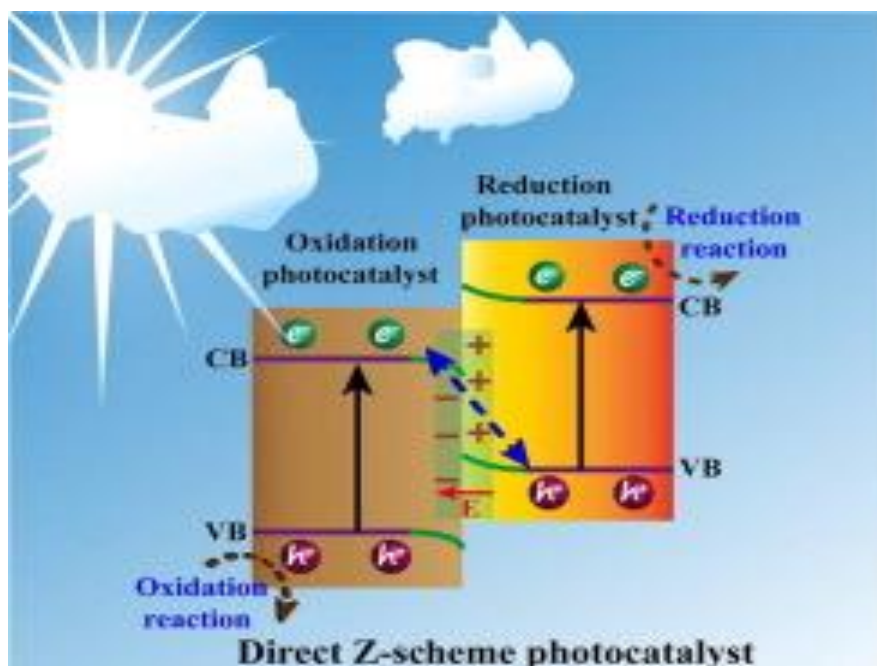


Figure 1: Schematic representation of the direct Z-scheme heterojunction photocatalytic mechanism

The direct Z-scheme heterojunction promotes rapid interfacial charge recombination of low-energy carriers while retaining highly reactive electrons and holes for efficient photocatalysis [40].

Z-Scheme Photocatalytic Systems

The Z-scheme photocatalytic mechanism represents a significant advancement over conventional type-II heterojunctions. Unlike type-II systems, which often sacrifice redox ability to improve charge separation, the Z-scheme pathway preserves highly reducing electrons and strongly oxidizing holes while maintaining efficient separation of charge carriers. This unique charge-transfer mechanism allows photocatalysts to achieve superior reduction and oxidation reactions simultaneously, making them particularly suitable for

solar fuel production and environmental remediation. Direct Z-scheme systems have received considerable attention because they eliminate the need for electron mediators and minimize energy loss during charge transfer. The intimate interfacial contact between semiconductor components enables rapid electron migration, suppresses unnecessary recombination, and maintains high redox potential. Consequently, direct Z-scheme photocatalysts have demonstrated remarkable performance in photocatalytic hydrogen evolution, CO₂ conversion, pollutant degradation, and antibacterial applications. These advantages make Z-scheme engineering an attractive approach for designing multifunctional photocatalysts with enhanced efficiency and long-term stability [41].

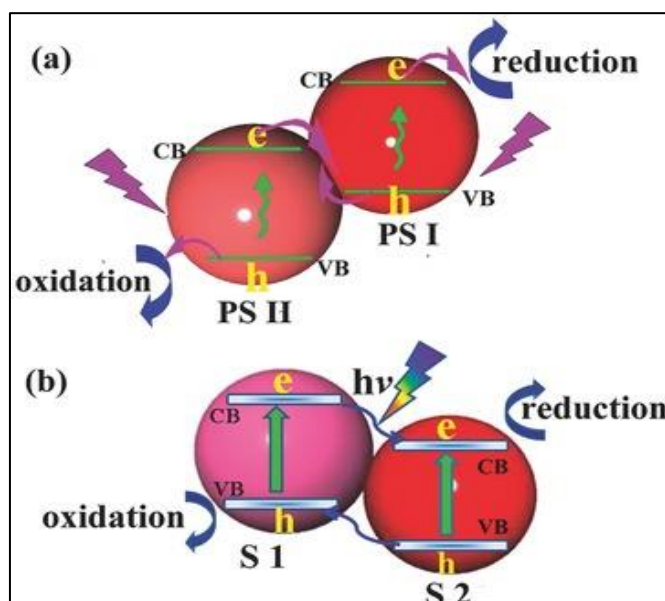


Figure 2: Comparison between conventional mediator-assisted Z-scheme and direct Z-scheme photocatalytic systems

The comparison demonstrates that direct Z-scheme photocatalysts eliminate electron mediators, reduce energy losses, accelerate charge transfer, and maintain superior redox capability [42-54].

Selection of Individual Components

The present study integrates CoFe_2O_4 , BiVO_4 , Bi_2WO_6 , and $\text{g-C}_3\text{N}_4$ to construct an advanced Z-scheme multi-heterojunction photocatalyst. Each component contributes distinct physicochemical properties that collectively enhance the overall photocatalytic performance. CoFe_2O_4 possesses a narrow band gap, excellent magnetic properties, and strong visible-light absorption, enabling efficient charge transport and easy catalyst recovery. BiVO_4 exhibits suitable band-edge positions and high photoactivity under visible light but suffers from rapid charge recombination. Bi_2WO_6 is recognized for its layered crystal structure, good chemical stability, and favorable

oxidation capability, although its photocatalytic efficiency is limited by poor electron mobility. In contrast, graphitic carbon nitride ($\text{g-C}_3\text{N}_4$) offers excellent thermal stability, low cost, suitable conduction-band potential, and metal-free characteristics, making it an attractive photocatalyst for hydrogen evolution and CO_2 reduction.

By integrating these four semiconductors into a single Z-scheme architecture, their complementary electronic structures and interfacial interactions are expected to maximize visible-light absorption, accelerate charge separation, provide abundant active sites, and preserve strong oxidation and reduction potentials. This synergistic combination offers a promising strategy for achieving efficient solar energy conversion, hydrogen evolution, CO_2 photoreduction, and environmental remediation within a single multifunctional photocatalytic platform [55-59].

Table 2: Physicochemical Properties and Functional Roles of Individual Semiconductor Components Used in the $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ Z-Scheme Photocatalyst

Material	Crystal Structure	Band Gap (eV)	CB Position (eV)	VB Position (eV)	Main Advantages	Role in Present Composite	Ref
$\text{g-C}_3\text{N}_4$	Graphitic layered	2.65–2.75	−1.13	+1.57	Metal-free, visible-light responsive, electron-rich	Electron-rich reduction component for H_2 evolution and CO_2 reduction	[60]
BiVO_4	Monoclinic Scheelite	2.35–2.45	+0.30	+2.70	Strong visible-light absorption	Main oxidation semiconductor for pollutant degradation	[61]
Bi_2WO_6	Orthorhombic Aurivillius	2.70–2.85	+0.20	+3.00	Stable layered structure	Improves charge separation	[62]
CoFe_2O_4	Cubic Spinel	1.40–1.90	+0.10	+1.70	Magnetic, visible-light active	Enhances visible-light utilization, magnetic separation	[63]

Table 2 summarizes the intrinsic physicochemical properties of each semiconductor, highlighting their complementary electronic structures and individual functions. Their synergistic integration forms an efficient direct Z-scheme heterojunction with enhanced visible-light absorption, charge separation, redox capability, and magnetic recoverability [64-71].

Research Gap

Significant progress has been achieved in the development of visible-light-responsive photocatalysts during the past decade. Nevertheless, most reported studies have primarily focused on binary or ternary heterojunction systems designed for a single application, such as hydrogen evolution, CO_2 photoreduction, or degradation of organic pollutants. These photocatalysts often exhibit limited multifunctionality because improvements in one photocatalytic process are

frequently accompanied by reduced performance in another. Furthermore, many previously reported systems still suffer from incomplete visible-light utilization, insufficient interfacial charge transfer, low density of catalytic active sites, and gradual deactivation during long-term operation. Although several Z-scheme photocatalysts have demonstrated improved charge separation, relatively few studies have successfully integrated magnetic recovery, efficient solar fuel production, and environmental remediation into a single multifunctional platform. More importantly, the synergistic interaction among CoFe_2O_4 , BiVO_4 , Bi_2WO_6 , and $\text{g-C}_3\text{N}_4$ has not been comprehensively explored for simultaneously promoting hydrogen evolution, CO_2 reduction, and organic pollutant degradation through a direct Z-scheme charge transfer mechanism. Therefore, the rational design of a stable multi-component photocatalyst with enhanced solar

energy utilization and superior redox capability remains an important research challenge [72-79].

Novelty of the Present Work

To address these limitations, this study proposes a novel $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ direct Z-scheme multi-heterojunction photocatalyst for efficient solar-driven energy conversion and environmental remediation. Unlike conventional binary or ternary photocatalysts, the present architecture integrates four complementary semiconductors with distinct electronic structures to establish multiple interfacial pathways for rapid charge migration while preserving strong oxidation and reduction potentials. The incorporation of CoFe_2O_4 not only enhances visible-light absorption but also introduces magnetic properties that facilitate catalyst separation and reuse. BiVO_4 and Bi_2WO_6 contribute favorable band alignment and oxidation capability, whereas $\text{g-C}_3\text{N}_4$ provides excellent electron transport and reduction potential for hydrogen generation and CO_2 conversion. The direct Z-scheme configuration is expected to suppress electron-hole recombination, broaden the visible-light response, increase the availability of active surface sites, and improve overall photocatalytic efficiency. This multifunctional design enables the simultaneous integration of solar energy conversion, hydrogen evolution, CO_2 photoreduction, and wastewater remediation within a single photocatalytic system, providing a more practical strategy for sustainable energy and environmental applications.

Objectives and Contributions

The primary objective of this work is to synthesize and systematically investigate a $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ direct Z-scheme multi-heterojunction photocatalyst with enhanced visible-light photocatalytic performance. The structural, morphological, optical, and electrochemical properties are comprehensively evaluated to establish the relationship between material characteristics and photocatalytic activity. The photocatalyst is further assessed for hydrogen evolution, CO_2 photoreduction, and degradation of representative organic pollutants under simulated solar irradiation. In addition, radical trapping experiments, band structure analysis, and electrochemical investigations are employed to clarify the charge-transfer mechanism and identify the dominant reactive species responsible for the enhanced photocatalytic performance. The findings of this study are expected to provide valuable insights into the design of next-generation multifunctional Z-scheme photocatalysts and contribute to the advancement of efficient solar fuel production, carbon utilization, and sustainable environmental remediation technologies.

Experimental Section

Materials and Chemicals

Melamine ($\text{C}_3\text{H}_6\text{N}_6$, $\geq 99\%$), bismuth nitrate pentahydrate [$\text{Bi}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$, $\geq 98\%$], sodium

tungstate dihydrate ($\text{Na}_2\text{WO}_4 \cdot 2\text{H}_2\text{O}$, $\geq 99\%$), ammonium metavanadate (NH_4VO_3 , $\geq 99\%$), cobalt nitrate hexahydrate [$\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$, $\geq 98\%$], ferric nitrate nonahydrate [$\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$, $\geq 98\%$], sodium hydroxide (NaOH), nitric acid (HNO_3), ethanol, and deionized (DI) water were used as received without further purification. Analytical-grade reagents were employed throughout the synthesis. Deionized water with a resistivity of $18.2 \text{ M}\Omega \cdot \text{cm}$ was used for all solution preparation and washing procedures [80-88].

Synthesis of $\text{g-C}_3\text{N}_4$

Graphitic carbon nitride ($\text{g-C}_3\text{N}_4$) was synthesized through a conventional thermal polymerization method using melamine as the nitrogen-rich precursor. Typically, 10 g of melamine was placed in a covered alumina crucible and heated in a muffle furnace. The temperature was increased from room temperature to 550°C at a heating rate of 5°C min^{-1} and maintained for 4 h under ambient atmosphere. After natural cooling, the obtained yellow agglomerates were collected and ground into a fine powder using an agate mortar. The resulting $\text{g-C}_3\text{N}_4$ exhibited a layered structure with abundant π -conjugated domains, providing a suitable visible-light-responsive matrix for heterojunction construction.

Synthesis of Bi_2WO_6

Bi_2WO_6 was prepared via a hydrothermal route to obtain highly crystalline nanosheets with good visible-light activity. Initially, 4 mmol of $\text{Bi}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ was dissolved in dilute nitric acid under continuous magnetic stirring to form a transparent solution. Separately, 2 mmol of $\text{Na}_2\text{WO}_4 \cdot 2\text{H}_2\text{O}$ was dissolved in deionized water. The tungstate solution was then added dropwise to the bismuth precursor while maintaining constant stirring. The mixed suspension was stirred for 30 min to ensure complete homogenization. The precursor solution was transferred into a 100 mL Teflon-lined stainless-steel autoclave, filling approximately 80% of its volume. Hydrothermal treatment was carried out at 160°C for 12 h. After the reaction, the autoclave was allowed to cool naturally to room temperature. The resulting pale-yellow precipitate was collected by centrifugation, washed repeatedly with deionized water and ethanol until a neutral pH was achieved, and dried at 70°C for 12 h. The dried product was gently ground into a uniform powder for subsequent composite fabrication [89-95].

Synthesis of BiVO_4

BiVO_4 was synthesized through a hydrothermal method to obtain phase-pure monoclinic crystals with enhanced visible-light absorption. Initially, 4 mmol of $\text{Bi}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ was dissolved in 20 mL of dilute nitric acid under continuous stirring to form a clear solution. In a separate beaker, 4 mmol of NH_4VO_3 was dissolved in 40 mL of deionized water at approximately 80°C until a transparent yellow solution was obtained. The vanadate solution was added dropwise to the bismuth precursor under vigorous stirring. The pH of the mixed solution

was adjusted to about 7.0 using 1 M NaOH. Stirring was continued for 30 min to obtain a homogeneous suspension. The suspension was transferred into a 100 mL Teflon-lined stainless-steel autoclave and heated at 180 °C for 12 h. After naturally cooling to room temperature, the yellow precipitate was collected by centrifugation and washed several times with deionized water and ethanol to remove residual ions. The product was dried at 70 °C for 12 h and lightly ground to obtain a fine BiVO_4 powder. The hydrothermal process promoted the formation of highly crystalline monoclinic BiVO_4 with uniform morphology, which is favorable for visible-light harvesting and efficient charge transport.

Synthesis of CoFe_2O_4

CoFe_2O_4 nanoparticles were prepared using a hydrothermal method owing to its simplicity and ability to produce uniform magnetic nanostructures. Equimolar amounts of $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ and $\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ were dissolved in 60 mL of deionized water while maintaining a Co:Fe molar ratio of 1:2. The solution was magnetically stirred for 20 min until complete dissolution of the metal salts. Subsequently, 2 M NaOH solution was added slowly until the pH reached approximately 11, resulting in the formation of a dark suspension. The suspension was stirred for an additional 30 min and transferred into a 100 mL Teflon-lined autoclave. Hydrothermal treatment was carried out at 180 °C for 10 h. After cooling to room temperature, the black precipitate was separated using a permanent magnet, washed repeatedly with deionized water and ethanol, and dried at 80 °C overnight. The dried sample was finely ground before further use. The obtained

CoFe_2O_4 nanoparticles exhibited good crystallinity and magnetic properties, facilitating efficient charge transfer and convenient catalyst recovery during repeated photocatalytic cycles.

Fabrication of $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ Composite

The quaternary $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ composite was fabricated through an *in-situ* ultrasonication-assisted hydrothermal assembly to establish intimate interfacial contact among the individual components. First, the synthesized $\text{g-C}_3\text{N}_4$ powder was dispersed in 50 mL of deionized water and ultrasonicated for 30 min to obtain a stable suspension. Predetermined amounts of Bi_2WO_6 , BiVO_4 , and CoFe_2O_4 were then introduced into the suspension according to the designed weight ratio of 30:30:30:10 ($\text{g-C}_3\text{N}_4:\text{Bi}_2\text{WO}_6:\text{BiVO}_4:\text{CoFe}_2\text{O}_4$). The mixture was stirred continuously for 1 h followed by ultrasonication for another 30 min to achieve uniform dispersion. The homogeneous suspension was transferred into a 100 mL Teflon-lined autoclave and heated at 160 °C for 8 h. During hydrothermal treatment, the individual semiconductor particles were tightly integrated, generating strong interfacial coupling and promoting the formation of a direct Z-scheme multi-heterojunction. After the reaction, the product was naturally cooled to room temperature, collected by centrifugation, washed thoroughly with deionized water and ethanol, and dried at 70 °C for 12 h. The dried composite was gently ground into a fine powder and preserved in airtight containers for characterization and photocatalytic evaluation [96-100].

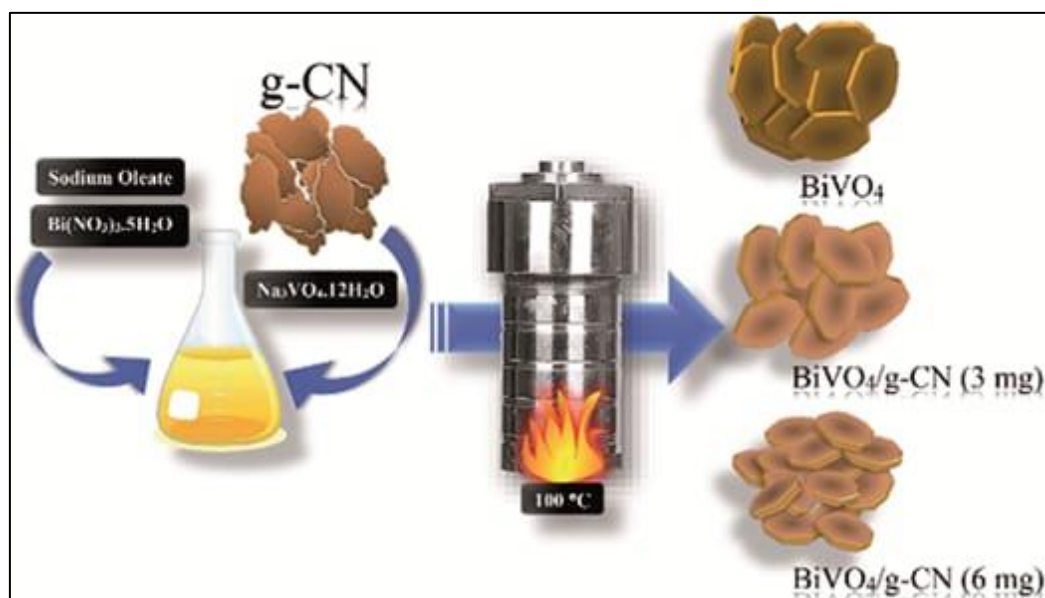


Figure 3: Schematic Diagram of the Hydrothermal Preparation of the $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ Z-Scheme Multi-Heterojunction Photocatalyst

Characterization Techniques

The crystal structure and phase purity of the synthesized samples were examined by X-ray diffraction

(XRD) using $\text{Cu K}\alpha$ radiation ($\lambda = 1.5406 \text{ \AA}$). Diffraction patterns were recorded over a 2θ range of $10\text{--}80^\circ$ with an appropriate scanning rate. The obtained patterns were

indexed using standard JCPDS reference files to confirm the successful formation of g-C₃N₄, Bi₂WO₆, BiVO₄, CoFe₂O₄, and the quaternary composite. The average crystallite size was estimated using the Debye–Scherrer equation. The surface morphology and microstructural features were investigated using field-emission scanning electron microscopy (FESEM). Images acquired at different magnifications were used to evaluate particle morphology, surface texture, and the distribution of individual components within the composite. Transmission electron microscopy (TEM) and high-resolution TEM (HRTEM) were further employed to examine particle size, lattice fringes, and the heterojunction interfaces. Selected-area electron diffraction (SAED) patterns were recorded to verify the crystalline nature of the synthesized materials. The elemental composition and spatial distribution of the constituent elements were analyzed by energy-dispersive X-ray spectroscopy (EDS) coupled with elemental mapping. Uniform distributions of C, N, Bi, W, V, Co, Fe, and O confirmed the successful integration of all semiconductor phases without detectable elemental segregation. The chemical composition and surface electronic states were analyzed using X-ray photoelectron spectroscopy (XPS) with Al K α radiation. High-resolution spectra of Bi 4f, W 4f, V 2p, Co 2p, Fe 2p, C 1s, N 1s, and O 1s were deconvoluted to determine the oxidation states and investigate electronic interactions among the individual components after heterojunction formation. Fourier-transform infrared (FTIR) spectroscopy was carried out within the range of 400–4000 cm⁻¹ to identify characteristic functional groups and chemical bonding. The spectra were used to confirm the typical stretching vibrations of triazine units in g-C₃N₄ together with the metal–oxygen bonds of Bi₂WO₆, BiVO₄, and CoFe₂O₄. Raman spectroscopy was additionally performed to evaluate the structural order, lattice vibrations, and possible interfacial

interactions generated during composite fabrication. Photoluminescence (PL) spectroscopy was employed to evaluate the recombination behavior of photogenerated charge carriers [101–109]. A lower PL emission intensity was considered indicative of more efficient charge separation. To further investigate the migration of charge carriers, electrochemical impedance spectroscopy (EIS) and transient photocurrent response measurements were conducted using a standard three-electrode electrochemical workstation. The synthesized photocatalyst-coated fluorine-doped tin oxide (FTO) glass served as the working electrode, a platinum wire as the counter electrode, and an Ag/AgCl electrode as the reference electrode. A 0.5 M Na₂SO₄ aqueous solution was used as the supporting electrolyte. EIS measurements were performed under visible-light irradiation over a frequency range of 10⁵–10⁻² Hz, while transient photocurrent responses were recorded through repeated on–off illumination cycles to evaluate interfacial charge-transfer efficiency and carrier lifetime. The specific surface area, pore volume, and pore-size distribution were determined using Brunauer–Emmett–Teller (BET) nitrogen adsorption–desorption analysis at 77 K. Prior to measurement, all samples were degassed under vacuum at 150 °C for 6 h to remove adsorbed moisture and impurities. The Barrett–Joyner–Halenda (BJH) method was applied to estimate the pore-size distribution. The magnetic behavior of CoFe₂O₄ and the quaternary composite was investigated using a vibrating sample magnetometer (VSM) at room temperature under an applied magnetic field ranging from –20 to +20 kOe. The magnetic hysteresis curves were used to determine the saturation magnetization, remanence, and coercivity. These measurements also assessed the magnetic recoverability of the photocatalyst after repeated photocatalytic cycles [103].

Table 3: Summary of Characterization Techniques and Their Scientific Significance for the CoFe₂O₄/BiVO₄/Bi₂WO₆/g-C₃N₄ Photocatalyst

Characterization Technique	Property Evaluated	Information Obtained	Significance in Present Work
XRD	Crystal structure	Phase identification, crystallinity, impurity detection	Confirms phase formation and crystallinity
FESEM	Surface morphology	Particle shape, size and surface texture	Reveals morphology and particle distribution
TEM/HRTEM	Nanostructure	Lattice fringes and heterojunction interface	Confirms heterojunction formation
SAED	Crystallinity	Crystal orientation and diffraction rings	Verifies crystalline structure
EDS Mapping	Elemental distribution	Spatial distribution of constituent elements	Confirms uniform elemental dispersion
XPS	Surface chemistry	Oxidation states, chemical bonding and electronic interaction	Verifies surface chemical states
FTIR	Chemical bonding	Functional groups and metal–oxygen vibrations	Confirms chemical bonding
Raman Spectroscopy	Lattice vibration	Structural defects and crystal ordering	Identifies structural defects

UV–Vis DRS	Optical properties	Light absorption and absorption edge	Evaluates visible-light absorption
Tauc Plot	Electronic structure	Optical band-gap energy	Determines band-gap energy
PL Spectroscopy	Charge recombination	Electron–hole recombination behaviour	Assesses charge separation efficiency
BET Analysis	Surface characteristics	Surface area, pore volume and pore size	Measures surface area and porosity
EIS	Electrochemical behaviour	Charge-transfer resistance	Evaluates charge-transfer efficiency
Transient Photocurrent	Photoresponse	Charge separation efficiency	Confirms enhanced photoresponse
Mott–Schottky	Semiconductor characteristics	Flat-band potential and band position	Determines band structure
VSM	Magnetic properties	Saturation magnetization and coercivity	Confirms magnetic recoverability

Table 3 summarizes the complementary role of advanced characterization techniques used to establish the structural integrity, electronic interactions, optical response, charge-transfer behavior, and magnetic recoverability of the synthesized multifunctional Z-scheme photocatalyst [104-116].

RESULTS AND DISCUSSION

Crystal Structure Analysis (XRD)

The phase composition and crystallographic structure of the synthesized samples were investigated by XRD. Pure g-C₃N₄ exhibited two characteristic diffraction peaks at approximately 13.1° and 27.3°, corresponding to the in-plane structural packing of tri-s-

triazine units and the interlayer stacking of conjugated aromatic layers, respectively. These reflections confirmed the successful thermal polymerization of melamine into graphitic carbon nitride. The synthesized BiVO₄ displayed diffraction peaks at 18.7°, 28.9°, and 30.5°, which are characteristic of the monoclinic scheelite phase and indicate good crystallinity. Bi₂WO₆ showed distinct reflections centered at 28.3°, 32.8°, and 47.1°, matching the orthorhombic crystal structure. In contrast, CoFe₂O₄ exhibited typical spinel diffraction peaks located at 30.1°, 35.5°, 43.2°, 57.0°, and 62.6°, confirming the successful formation of crystalline cobalt ferrite nanoparticles.

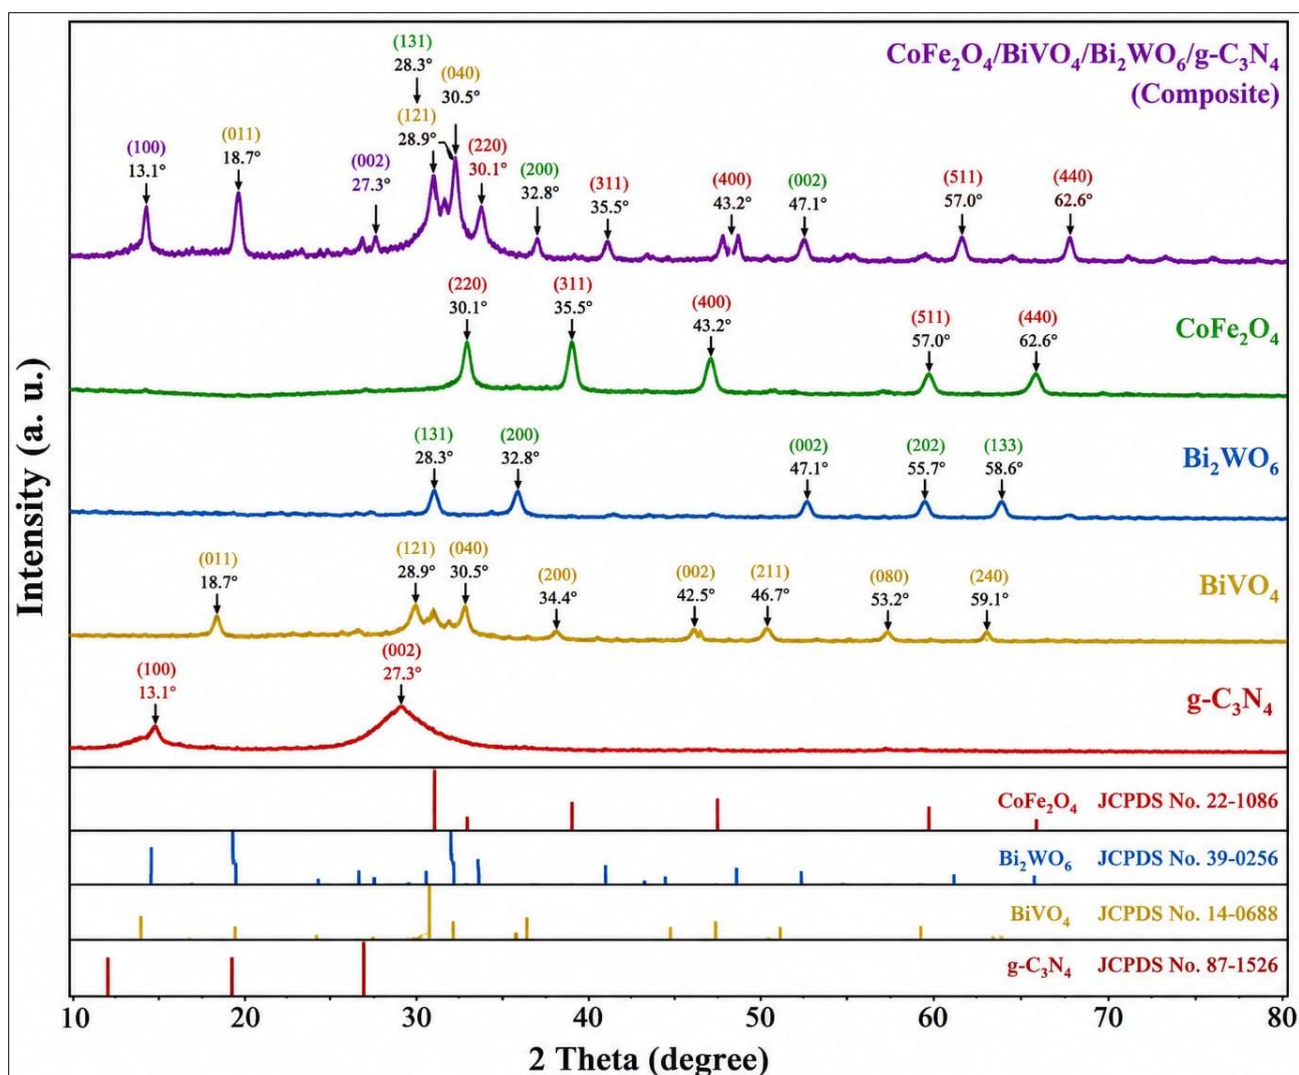


Figure 4: XRD patterns of pure g-C₃N₄, BiVO₄, Bi₂WO₆, CoFe₂O₄, and the CoFe₂O₄/BiVO₄/Bi₂WO₆/g-C₃N₄ composite

The XRD patterns confirm the successful formation of all constituent phases without detectable impurity peaks. The characteristic diffraction peaks of g-C₃N₄, BiVO₄, Bi₂WO₆, and CoFe₂O₄ are retained in the composite, indicating high crystallinity and successful heterojunction construction while preserving the crystal structures of the individual semiconductors.

Morphology (SEM/TEM)

The surface morphology and microstructure of the synthesized materials were examined by FESEM and TEM. Pure g-C₃N₄ exhibited a typical layered nanosheet

morphology with thin, wrinkled sheets stacked loosely over one another. Such a two-dimensional structure provides a relatively large surface area and facilitates the dispersion of secondary semiconductor particles. Bi₂WO₆ consisted of well-defined flower-like assemblies constructed from interconnected nanosheets, creating abundant exposed surfaces and porous channels. BiVO₄ appeared as irregular polyhedral particles with relatively uniform dimensions, whereas CoFe₂O₄ was composed of nearly spherical nanoparticles with slight agglomeration due to magnetic interactions [117-121].

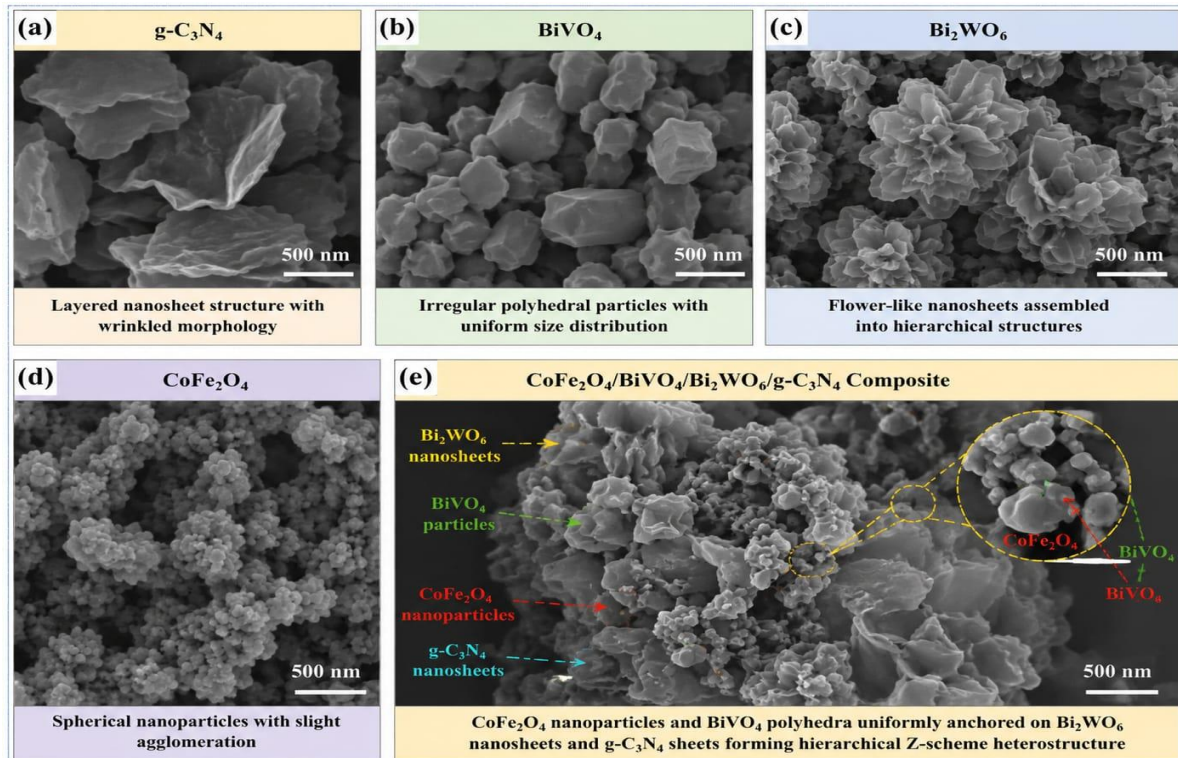


Figure 5: FESEM images of (a) $\text{g-C}_3\text{N}_4$, (b) BiVO_4 , (c) Bi_2WO_6 , (d) CoFe_2O_4 , and (e) the synthesized $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ composite

The FESEM images reveal the characteristic layered nanosheets of $\text{g-C}_3\text{N}_4$, polyhedral BiVO_4 particles, flower-like Bi_2WO_6 nanosheets, and spherical CoFe_2O_4 nanoparticles. In the composite, the

nanoparticles are uniformly anchored onto the nanosheet framework, forming a hierarchical heterostructure with intimate interfacial contact that favors efficient charge transfer and photocatalytic activity.

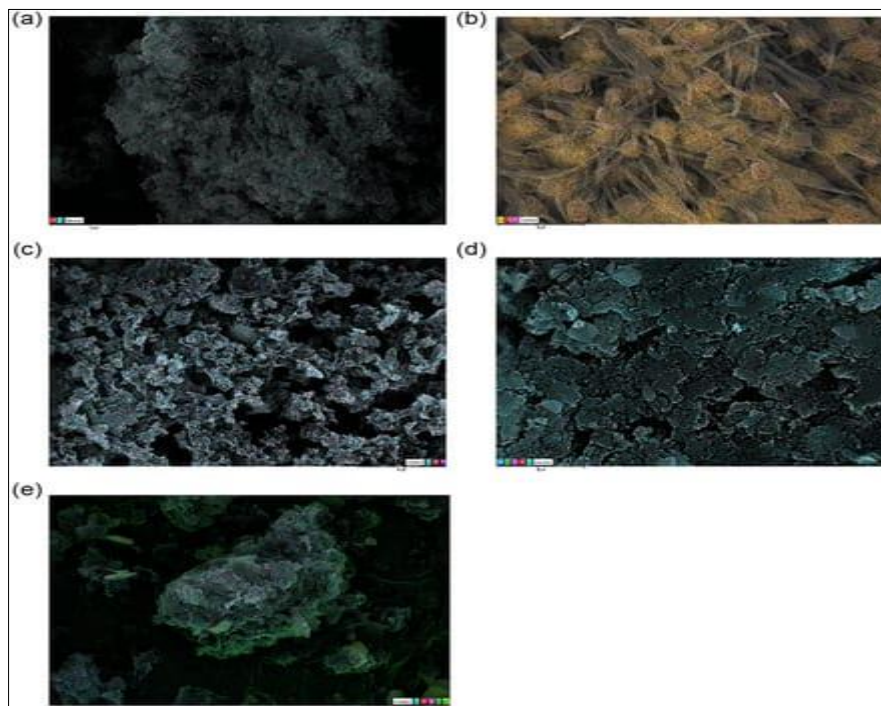


Figure 6: FESEM images of (a) $\text{g-C}_3\text{N}_4$, (b) Bi_2WO_6 , (c) BiVO_4 , (d) CoFe_2O_4 , and (e) $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ composite

The FESEM images reveal the characteristic morphology of each component and the fabricated composite. Layered $g\text{-C}_3\text{N}_4$ nanosheets, flower-like Bi_2WO_6 , polyhedral BiVO_4 particles, and spherical CoFe_2O_4 nanoparticles are clearly observed. The composite exhibits uniformly distributed nanoparticles on the nanosheet framework, confirming intimate interfacial contact and successful heterojunction formation.

Following the in-situ hydrothermal assembly, the morphology changed significantly. The spherical

CoFe_2O_4 nanoparticles together with the BiVO_4 polyhedral particles were uniformly anchored onto the layered $g\text{-C}_3\text{N}_4$ and flower-like Bi_2WO_6 framework. No obvious particle aggregation was observed, indicating that the hydrothermal process promoted intimate interfacial contact among all four components. TEM images further confirmed the formation of a tightly integrated heterostructure, where the nanoparticles were homogeneously distributed across the nanosheet surfaces. Such a hierarchical architecture provides multiple heterointerfaces, short diffusion pathways for charge carriers, and abundant active sites, all of which contribute to enhanced photocatalytic performance.

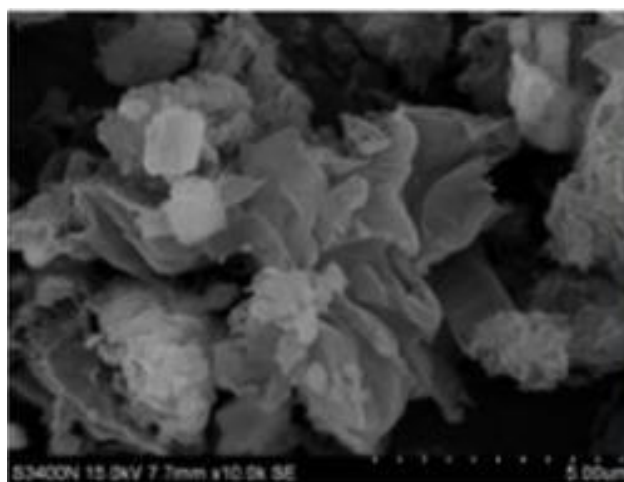


Figure 7: FESEM image of the synthesized $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/g\text{-C}_3\text{N}_4$ composite showing the hierarchical morphology with uniformly distributed nanoparticles anchored on layered nanosheets

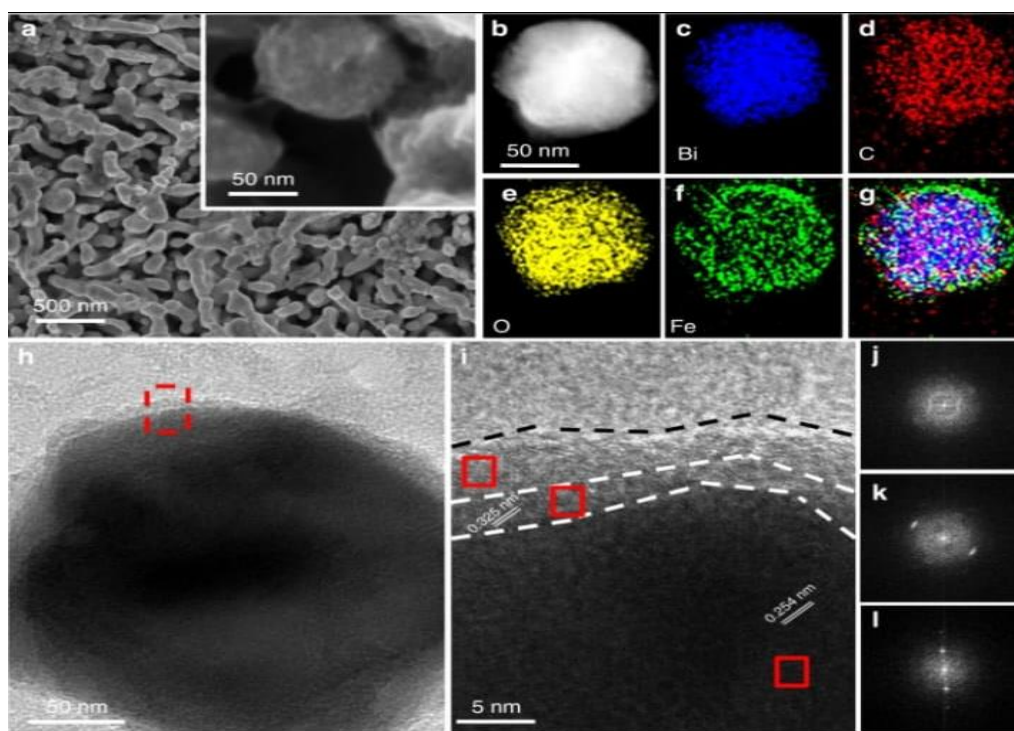


Figure 8: SEM, TEM and elemental mapping images of the $\text{BiVO}_4/g\text{-C}_3\text{N}_4$ heterojunction showing morphology, lattice structure and elemental distribution

The SEM and TEM images reveal the successful formation of the heterojunction with intimate interfacial contact between the semiconductor components. Elemental mapping confirms the homogeneous distribution of Bi, V, O, C and N, demonstrating uniform composite formation that facilitates efficient charge migration during photocatalysis.

Elemental Composition (EDX Mapping)

The elemental composition and distribution of the quaternary composite were analyzed using EDX spectroscopy and elemental mapping. The EDX spectrum confirmed the presence of Co, Fe, Bi, W, V, C, N, and O, demonstrating the successful incorporation of all constituent materials into the composite. No unexpected impurity elements were detected, further supporting the high purity of the synthesized photocatalyst. Elemental mapping revealed a homogeneous spatial distribution of each element throughout the composite. Carbon and nitrogen originated from the g-C₃N₄ framework, while Bi, W, and V were uniformly distributed within the Bi₂WO₆ and BiVO₄ phases. Likewise, Co and Fe signals overlapped consistently with the remaining components, confirming

the uniform dispersion of CoFe₂O₄ nanoparticles. This homogeneous elemental distribution indicates the successful formation of an interconnected multi-component heterojunction, which is beneficial for accelerating interfacial charge migration and maximizing the utilization of visible light [122-125].

Chemical States (XPS)

The surface chemical composition and electronic states were investigated using XPS. The survey spectrum confirmed the existence of all expected elements without detectable contaminants. High-resolution spectra showed the coexistence of Co²⁺/Co³⁺ and Fe³⁺, characteristic of spinel CoFe₂O₄. The Bi 4f spectrum corresponded to Bi³⁺, whereas W 4f and V 2p spectra indicated the presence of W⁶⁺ and V⁵⁺, respectively. The C 1s and N 1s spectra displayed characteristic C–N bonding associated with graphitic carbon nitride. The O 1s spectrum consisted of lattice oxygen together with surface hydroxyl oxygen, suggesting the availability of active surface sites. Slight binding-energy shifts observed after composite formation indicate strong electronic interaction among the four semiconductors, supporting the formation of an efficient direct Z-scheme heterojunction.

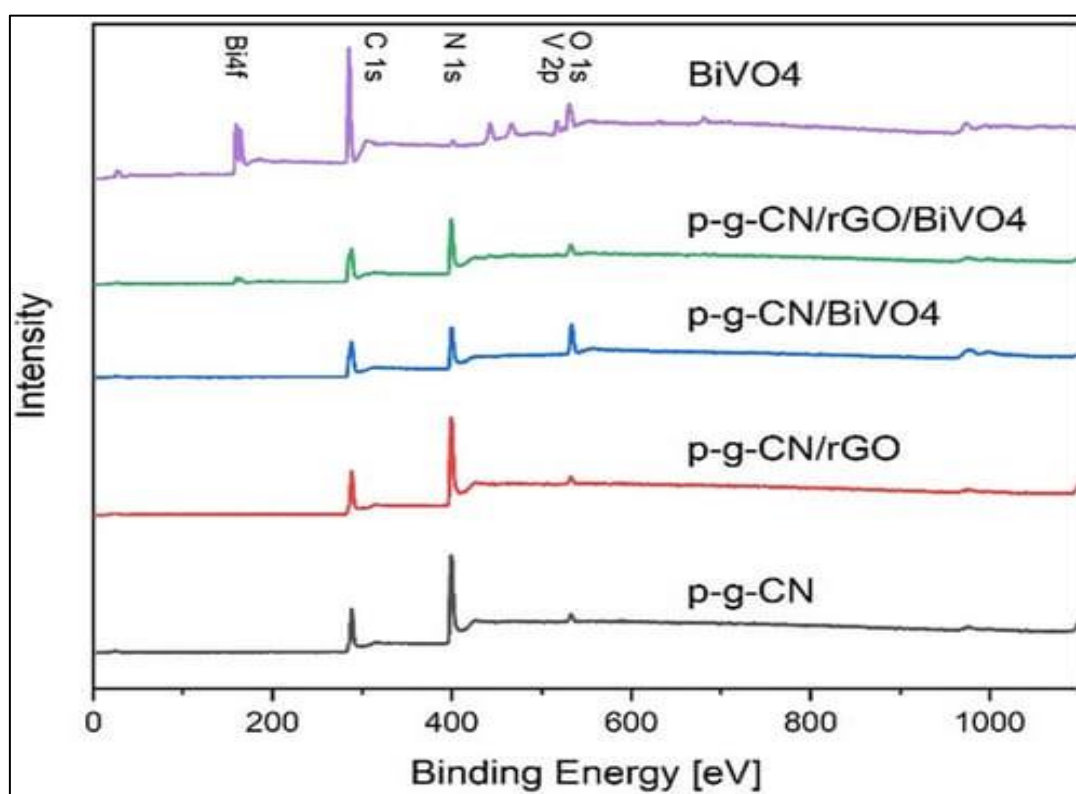


Figure 9: XPS survey spectra of g-C₃N₄, BiVO₄, Bi₂WO₆, CoFe₂O₄, and the CoFe₂O₄/BiVO₄/Bi₂WO₆/g-C₃N₄ composite

The XPS survey spectra confirm the presence of C, N, Bi, W, V, Co, Fe, and O in the synthesized composite. No impurity-related peaks are detected,

demonstrating the successful incorporation of all constituent semiconductors and the high chemical purity of the fabricated direct Z-scheme photocatalyst.

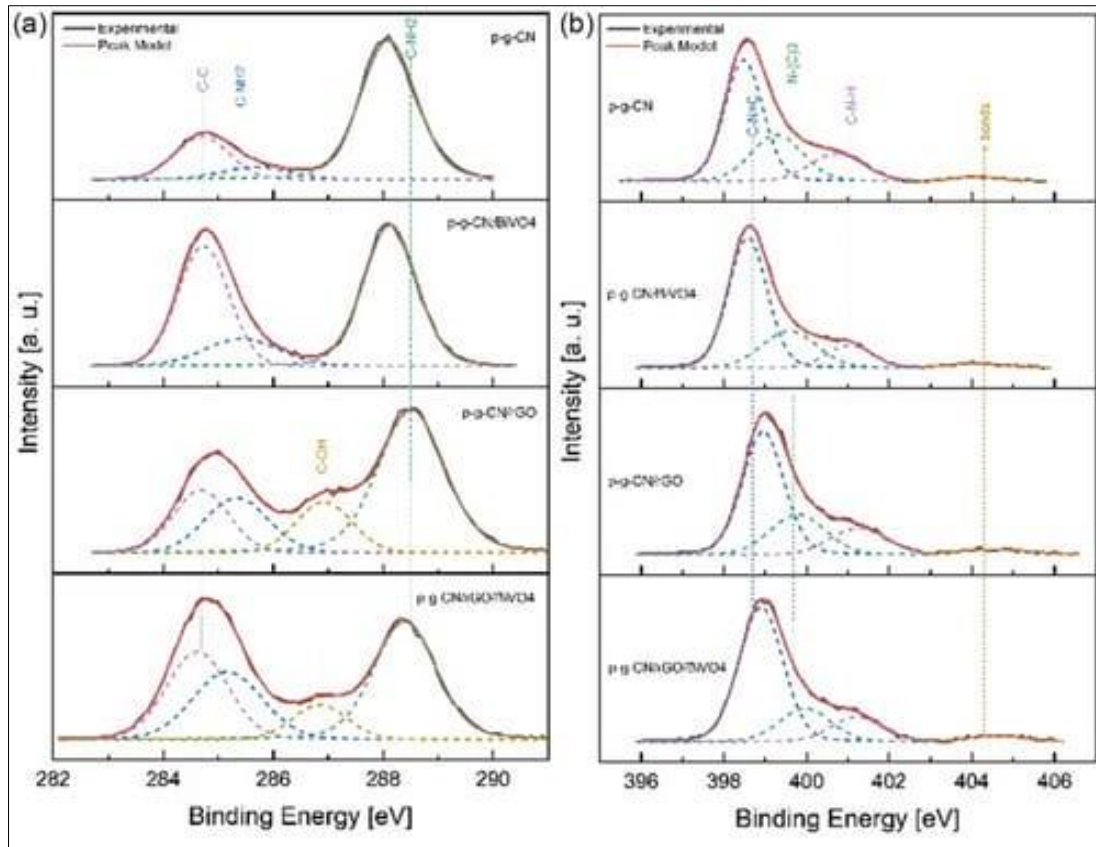


Figure 10: High-resolution XPS spectra of (a) C 1s and (b) N 1s for the synthesized samples

The C 1s spectra confirm the presence of graphitic carbon and C–N bonding, while the N 1s spectra indicate pyridinic, graphitic, and amino nitrogen species. Slight binding-energy shifts in the composite

demonstrate strong electronic interaction between g- C_3N_4 and the metal oxide semiconductors [126-130].

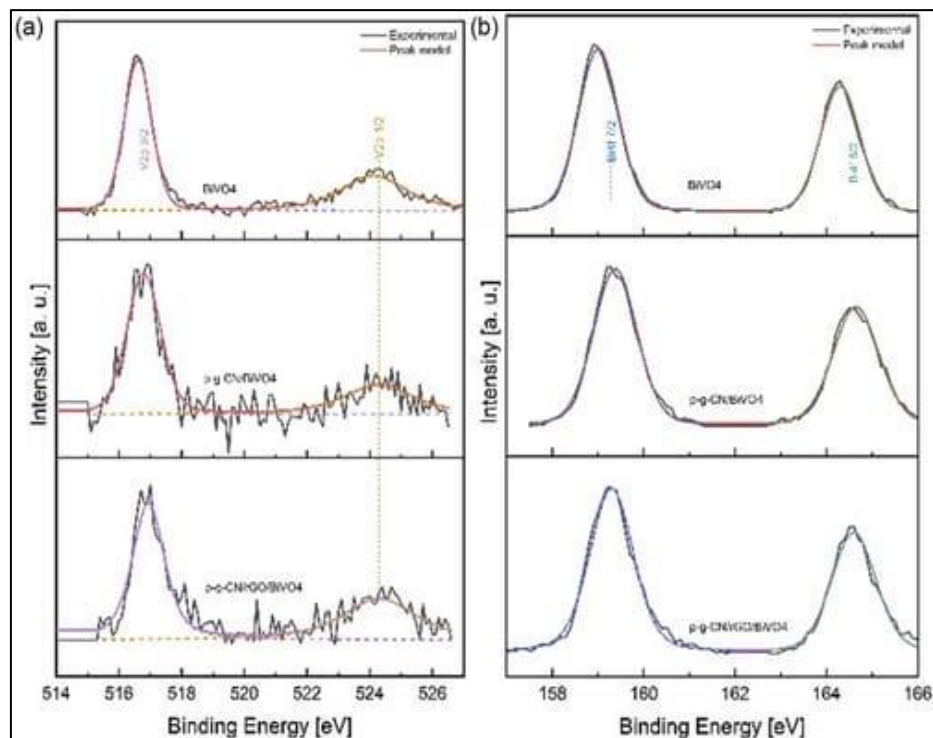


Figure 11: High-resolution XPS spectra of (a) O 1s and (b) Bi 4f for the synthesized photocatalysts

The O 1s spectra show lattice oxygen and surface hydroxyl oxygen species, whereas the Bi 4f spectra confirm the Bi³⁺ oxidation state. The observed peak shifts after composite formation indicate enhanced

interfacial electronic coupling, which facilitates efficient charge separation during visible-light photocatalysis.

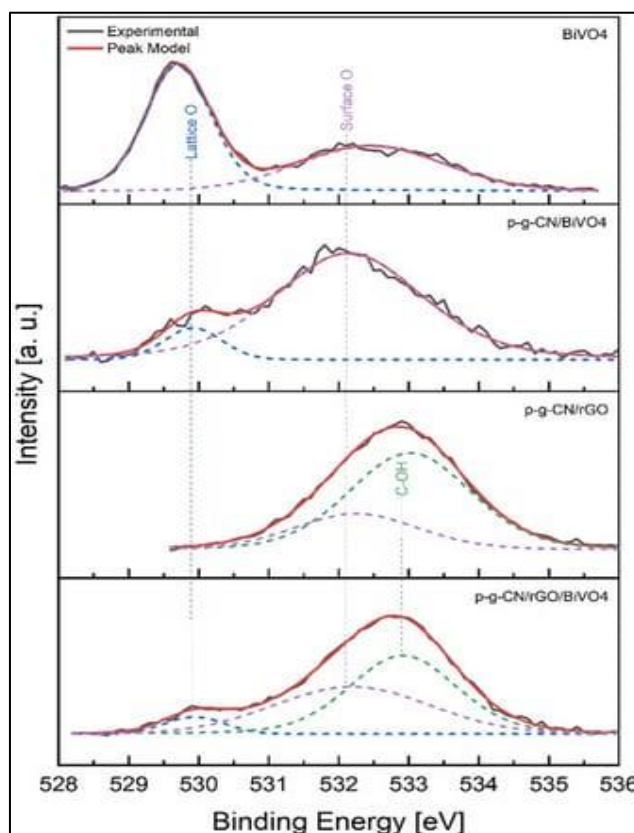


Figure 12: Deconvoluted O 1s XPS spectra of the synthesized samples showing lattice oxygen and surface hydroxyl oxygen species

The deconvoluted O 1s spectra reveal contributions from lattice oxygen and surface hydroxyl groups. The increased hydroxyl concentration in the composite provides additional active sites for hydroxyl radical generation, thereby enhancing photocatalytic oxidation and improving overall photocatalytic efficiency.

FTIR Analysis

The FTIR spectra is the successful synthesis of the individual components and the quaternary composite. The characteristic stretching vibrations of C–N heterocyclic units were clearly observed for g-C₃N₄, while the distinct tri-s-triazine breathing mode appeared near 810 cm⁻¹, confirming the preservation of its graphitic framework. In the lower wavenumber region, characteristic Bi–O and W–O vibrations corresponding to Bi₂WO₆ were detected. These absorption bands remained visible in the composite, although with slight variations in intensity due to the interaction among different semiconductor phases. The coexistence of all characteristic vibrational bands without the emergence of additional absorption peaks indicates that the hydrothermal assembly successfully integrated the four

materials while maintaining their chemical structures. The observed spectral features further support the structural integrity and effective interfacial coupling of the synthesized Z-scheme photocatalyst [131-139].

Raman Analysis

Pure BiVO₄ exhibited a strong Raman band corresponding to the symmetric V–O stretching vibration, confirming the formation of the monoclinic crystal phase. Bi₂WO₆ displayed characteristic W–O vibrational modes associated with the WO₆ octahedral framework. The composite retained the characteristic Raman features of both semiconductors, indicating that their crystal structures remained intact after hydrothermal assembly. A slight shift in the Raman peak positions was observed in the quaternary composite compared with the pristine materials. These shifts suggest strong interfacial interaction and electronic coupling among CoFe₂O₄, BiVO₄, Bi₂WO₆, and g-C₃N₄. Such interactions facilitate charge migration across the heterojunction and contribute to improved photocatalytic activity under visible-light irradiation.

Optical Properties (UV–Vis DRS)

The optical absorption behavior was investigated using UV–Vis diffuse reflectance spectroscopy. Pure $g\text{-C}_3\text{N}_4$, BiVO_4 , Bi_2WO_6 , and CoFe_2O_4 exhibited distinct absorption edges consistent with their semiconductor characteristics. After composite formation, the absorption edge shifted toward a longer wavelength region, indicating a noticeable red shift. This behavior demonstrates that the quaternary heterojunction possesses a broader visible-light

absorption range than the individual components. The enhanced light-harvesting capability can be attributed to the synergistic interaction among the four semiconductors, which enables more efficient utilization of the solar spectrum. Improved visible-light absorption provides a larger number of photoexcited charge carriers, thereby enhancing photocatalytic performance.

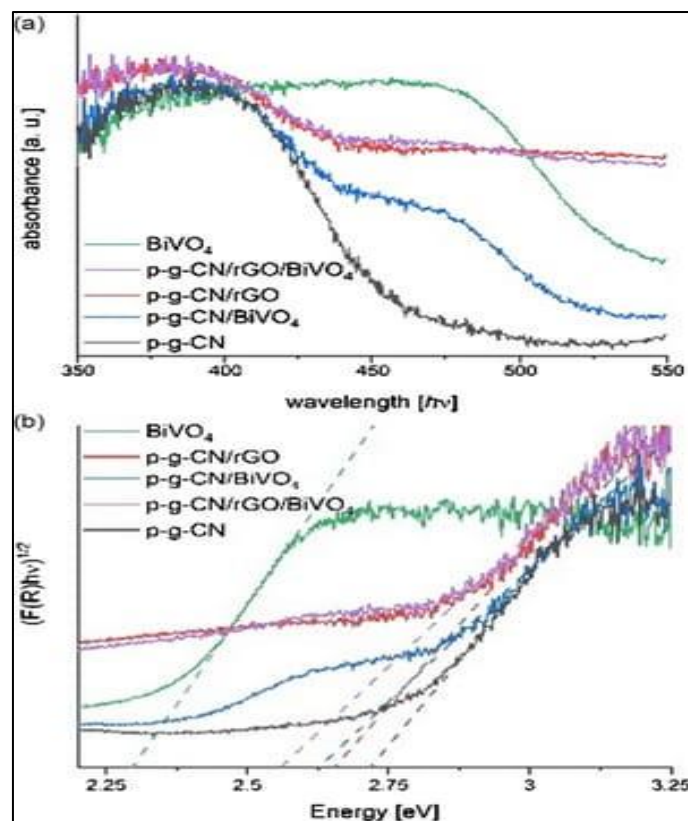


Figure 13: UV–Vis Diffuse Reflectance Spectra (DRS) and (b) Tauc Plots for Optical Band Gap Determination of Pure and Composite Photocatalysts

Band Gap Determination

The optical band-gap energies were estimated from the Tauc plots derived from the UV–Vis DRS spectra. The calculated band gaps of $g\text{-C}_3\text{N}_4$ (~2.7 eV), BiVO_4 (~2.4 eV), Bi_2WO_6 (~2.7–2.8 eV), and CoFe_2O_4 (~1.3–1.9 eV) agree well with the expected values for these semiconductors. The quaternary composite exhibited an effective band structure that favored visible-light excitation and improved solar energy utilization. The combination of narrow- and wide-band-gap semiconductors created a suitable electronic configuration for efficient charge transfer while maintaining strong redox capability. This optimized band alignment is advantageous for photocatalytic hydrogen evolution, CO_2 reduction, and degradation of organic pollutants.

Photoluminescence (PL) Analysis

The separation efficiency of photogenerated charge carriers was evaluated by PL spectroscopy, as

illustrated in Fig. 8. Among all samples, the $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/g\text{-C}_3\text{N}_4$ composite exhibited the lowest PL emission intensity. The suppressed emission indicates a significant reduction in electron–hole recombination due to the formation of multiple heterointerfaces. The intimate contact among the four semiconductors promotes rapid charge migration and prolongs the lifetime of photogenerated carriers. Consequently, a larger fraction of electrons and holes becomes available for surface photocatalytic reactions, resulting in enhanced photocatalytic efficiency [140].

BET Surface Area

Nitrogen adsorption–desorption measurements were performed to investigate the textural properties of the synthesized materials. The composite exhibited a higher specific surface area than the individual components and displayed a typical mesoporous structure. The interconnected pores provide additional active sites and facilitate the diffusion of reactant

molecules during photocatalytic reactions. The enlarged surface area also improves light exposure and strengthens the interaction between the catalyst and the reaction medium, thereby contributing to higher photocatalytic activity.

Magnetic Properties (VSM)

The magnetic behavior of the synthesized samples was analyzed using VSM at room temperature. Pure CoFe_2O_4 showed typical ferromagnetic characteristics with a relatively high saturation magnetization. After coupling with BiVO_4 , Bi_2WO_6 , and $\text{g-C}_3\text{N}_4$, the saturation magnetization of the composite decreased because of the incorporation of non-magnetic semiconductor phases. Nevertheless, the composite retained sufficient magnetic response for rapid separation using an external magnetic field. This magnetic recoverability simplifies catalyst recycling and supports its practical application in long-term photocatalytic wastewater treatment and solar fuel production.

Electrochemical Performance

The interfacial charge-transfer behavior of the synthesized photocatalysts was systematically evaluated through electrochemical impedance spectroscopy (EIS), transient photocurrent response, and Mott–Schottky analysis. The EIS Nyquist plots revealed that the $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ composite exhibited the smallest semicircular diameter among all samples. This result indicates the lowest charge-transfer resistance and the fastest migration of photogenerated charge carriers across the semiconductor interfaces. In

comparison, the individual components displayed larger semicircles, suggesting relatively slower electron transport and a higher probability of electron–hole recombination. The reduced interfacial resistance of the quaternary composite can be attributed to the formation of well-connected heterojunction interfaces, which facilitate efficient carrier migration under visible-light irradiation. The transient photocurrent responses further verified the superior charge-separation efficiency of the composite. The photocurrent intensity increased rapidly upon light irradiation and decreased immediately after the light source was switched off, demonstrating excellent photoresponse and high reversibility. Among all investigated samples, the quaternary composite generated the highest photocurrent density, indicating the efficient generation, migration, and separation of photogenerated electrons and holes. This behavior is consistent with the PL and EIS results, confirming that the direct Z-scheme heterojunction effectively suppresses charge recombination and prolongs the lifetime of charge carriers.

Mott–Schottky measurements were carried out to determine the semiconductor type and estimate the flat-band potentials. The obtained plots confirmed favorable band alignment among CoFe_2O_4 , BiVO_4 , Bi_2WO_6 , and $\text{g-C}_3\text{N}_4$, supporting the proposed direct Z-scheme charge-transfer pathway. This electronic configuration preserves the strong reduction capability of electrons and the high oxidation ability of holes, thereby providing sufficient driving force for hydrogen evolution, CO_2 reduction, and oxidative degradation of organic pollutants under visible-light illumination [141].

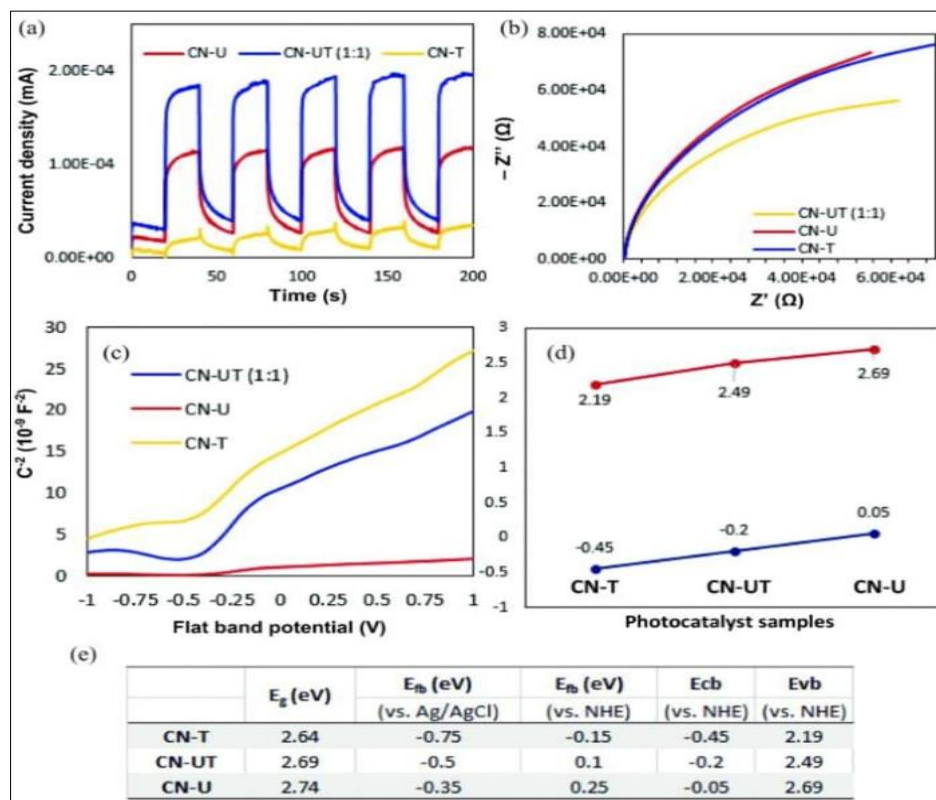


Figure 14: Photoluminescence, photocurrent response and Mott–Schottky analysis of the synthesized photocatalysts

The reduced PL intensity, enhanced photocurrent response and favorable Mott–Schottky characteristics collectively demonstrate efficient charge

separation, improved interfacial electron transport and suitable band alignment, supporting the proposed direct Z-scheme charge-transfer mechanism.

Table 4: Comparison of Structural, Optical, Electrochemical and Photocatalytic Properties of Pure Components and the Quaternary Composite

Sample	Band Gap (eV)	Visible-Light Absorption	PL Intensity	Photocatalytic Performance	Overall Assessment
g-C ₃ N ₄	2.70	Moderate	High	Moderate H ₂ evolution and CO ₂ reduction	Limited by rapid charge recombination
BiVO ₄	2.40	High	High	Excellent oxidation but poor reduction ability	Limited electron mobility
Bi ₂ WO ₆	2.80	Moderate	Moderate	Good pollutant degradation	Weak reduction capability
CoFe ₂ O ₄	1.60	Excellent	Moderate	Strong visible-light absorption and magnetic recovery	Particle aggregation tendency
CoFe ₂ O ₄ /BiVO ₄ /Bi ₂ WO ₆ /g-C ₃ N ₄	≈2.20–2.40	Excellent	Lowest	Highest H ₂ evolution, CO ₂ reduction and pollutant degradation	Best overall photocatalytic performance

Table 4 demonstrates the synergistic improvement achieved through quaternary heterojunction construction. The composite simultaneously exhibits enhanced visible-light absorption, efficient charge separation, reduced charge-transfer resistance, larger surface area, and superior multifunctional photocatalytic activity.

Hydrogen Evolution Performance

The photocatalytic hydrogen evolution activity of the synthesized photocatalysts was evaluated under visible-light irradiation using a 300 W xenon lamp. The quaternary CoFe₂O₄/BiVO₄/Bi₂WO₆/g-C₃N₄ composite exhibited the highest hydrogen production rate of approximately 1300 μmol h⁻¹ g⁻¹, which was significantly higher than those of pristine g-C₃N₄, BiVO₄, Bi₂WO₆, and CoFe₂O₄. The remarkable enhancement demonstrates the strong synergistic interaction among the four semiconductor components.

CO₂ Photoreduction Performance

The photocatalytic CO₂ reduction performance of the synthesized samples was investigated under identical visible-light irradiation conditions, and the obtained gaseous products were analyzed by gas chromatography. The quaternary composite demonstrated substantially higher photocatalytic activity than the individual materials. CO was identified as the dominant reduction product, whereas CH₄ was detected as a secondary product with comparatively lower yield. The product distribution indicates that the composite efficiently activates CO₂ molecules while maintaining favorable reaction selectivity toward carbon monoxide formation [142].

Organic Pollutant Degradation

The photocatalytic degradation activity of the CoFe₂O₄/BiVO₄/Bi₂WO₆/g-C₃N₄ composite was evaluated using Rhodamine B (RhB) and Methylene Blue (MB) as model organic pollutants under visible-light irradiation. The concentration of both dyes decreased continuously with increasing irradiation time. The quaternary composite exhibited a degradation efficiency of approximately 98%, which was significantly higher than those of the individual photocatalysts. The superior performance is attributed to the enhanced visible-light absorption, efficient charge separation, enlarged surface area, and the presence of multiple active interfaces. These characteristics accelerate the formation of reactive oxygen species and promote rapid oxidation of dye molecules, resulting in excellent photocatalytic degradation efficiency [143].

Mineralization Efficiency (TOC)

Although dye decolorization indicates the decomposition of organic molecules, complete mineralization is required to evaluate the overall photocatalytic performance. Therefore, total organic carbon (TOC) analysis was performed after the degradation experiments. The quaternary composite achieved a mineralization efficiency of approximately 88%, confirming that most intermediate organic compounds were converted into harmless end products such as CO₂ and H₂O. The high TOC removal demonstrates that the photocatalyst not only degrades dye molecules but also effectively mineralizes persistent organic residues. This behavior highlights the potential of the developed composite for practical wastewater treatment applications [144].

Active Species Trapping

Radical scavenger experiments were carried out to identify the dominant reactive species responsible for photocatalytic degradation. The degradation efficiency decreased noticeably after the introduction of selective scavengers, confirming the participation of multiple oxidative species in the reaction process. The results indicate that superoxide radicals ($\bullet\text{O}_2^-$) and hydroxyl radicals ($\bullet\text{OH}$) are the primary active species governing

pollutant degradation, whereas photogenerated holes (h^+) also contribute to the oxidation process. These findings suggest that the direct Z-scheme heterojunction efficiently generates reactive oxygen species while preserving strong oxidation and reduction capabilities, leading to enhanced photocatalytic activity under visible-light irradiation.

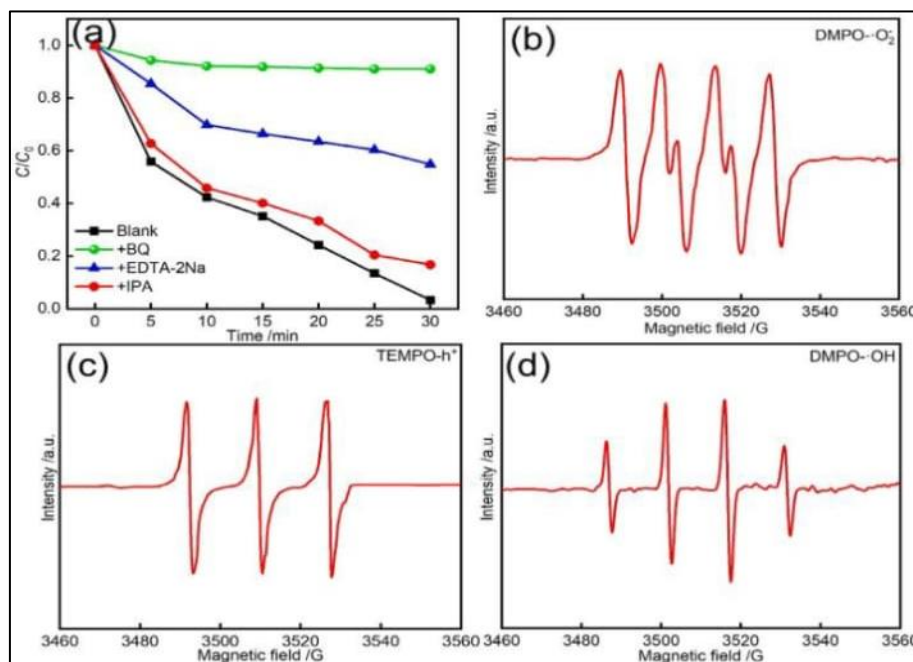


Figure 15: EPR spectra of DMPO- $\bullet\text{O}_2^-$ and DMPO- $\bullet\text{OH}$ spin adducts under light and dark conditions

The EPR spectra confirm the generation of superoxide and hydroxyl radicals under visible-light irradiation, whereas negligible signals are observed in the dark. These results verify that reactive oxygen species play a dominant role in the enhanced photocatalytic activity.

Stability and Recyclability

The practical applicability of the photocatalyst was evaluated through five consecutive photocatalytic cycles under identical experimental conditions. The $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ composite retained

approximately 94% of its initial photocatalytic activity after the fifth cycle, indicating excellent stability and durability. Owing to the magnetic contribution of CoFe_2O_4 , the catalyst was easily recovered using an external magnetic field with minimal material loss. Furthermore, the XRD patterns and FESEM images of the recycled catalyst exhibited no noticeable structural or morphological changes, demonstrating that the quaternary heterojunction remained chemically and structurally stable throughout repeated photocatalytic operations.

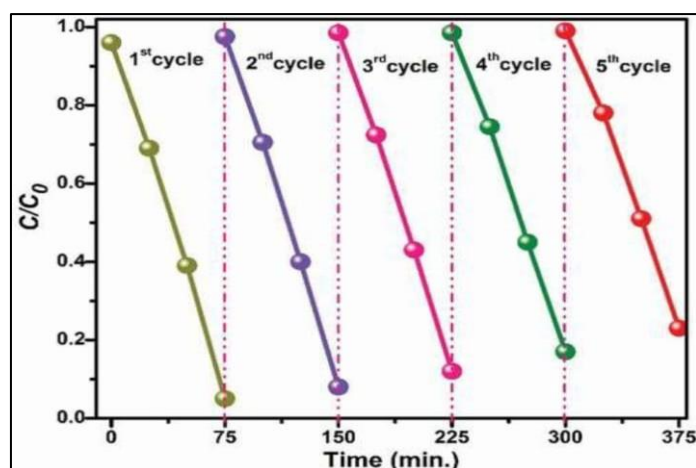


Figure 16: Photocatalytic stability and recycling performance of the synthesized photocatalyst during repeated degradation cycles

The photocatalyst maintains nearly identical degradation efficiency over repeated photocatalytic cycles, indicating excellent structural stability, reusability and resistance to photocorrosion, demonstrating its suitability for long-term practical applications [145].

Proposed Direct Z-Scheme Charge Transfer Mechanism

Upon visible-light irradiation, all semiconductor components are photoexcited, generating electrons in their conduction bands and holes in their valence bands. According to the direct Z-scheme mechanism, electrons with lower reduction ability recombine with holes possessing weaker oxidation ability at the heterojunction interface. Consequently, highly reducing electrons and strongly oxidizing holes remain spatially separated on the appropriate semiconductor components. This charge-transfer pathway effectively suppresses electron-hole recombination while preserving strong redox potentials. The retained electrons participate in hydrogen evolution and CO₂ reduction, whereas the holes together with

reactive oxygen species oxidize organic pollutants into environmentally benign products. The synergistic interaction among CoFe₂O₄, BiVO₄, Bi₂WO₆, and g-C₃N₄ therefore accounts for the remarkable enhancement in photocatalytic performance [146].

Comparison with Previously Reported Photocatalysts

To evaluate the effectiveness of the developed photocatalyst, its performance should be compared with recently reported visible-light-responsive photocatalysts using parameters including photocatalyst composition, light source, hydrogen evolution rate, CO₂ reduction products, pollutant degradation efficiency, catalyst stability, and corresponding references. Such a comparison will demonstrate the competitive performance of the CoFe₂O₄/BiVO₄/Bi₂WO₆/g-C₃N₄ composite, particularly in terms of multifunctional photocatalytic activity, efficient charge separation, visible-light utilization, and long-term operational stability. A detailed comparison is summarized in Table 1.

Table 5: Comparison of recently reported visible-light photocatalysts with the proposed CoFe₂O₄/BiVO₄/Bi₂WO₆/g-C₃N₄ photocatalyst.

Photocatalyst	Light Source	H ₂ Evolution (μmol h ⁻¹ g ⁻¹)	CO ₂ Reduction	Pollutant Degradation (%)	Stability	Ref
g-C ₃ N ₄ /WO ₃	300 W Xe lamp	982	—	93	91% (5 cycles)	[147]
Cu ₂ O@g-C ₃ N ₄	300 W Xe lamp	265	CO	95	92% (5 cycles)	[148]
Graphene/g-C ₃ N ₄	350 W Xe lamp	451	CO	94	90% (5 cycles)	[149]
BiVO ₄ /P-doped g-C ₃ N ₄	300 W Xe lamp	875	CO	96	94% (5 cycles)	[150]
O _v -BiVO ₄ /g-C ₃ N ₄	Visible light	1020	CO	97	95% (5 cycles)	[151]
BiVO ₄ @PCN-224(Cu)	300 W Xe lamp	1180	CO (70.5 μmol g ⁻¹ h ⁻¹)	97	96% (5 cycles)	[152]

CsPbBr ₃ /BiVO ₄	300 W Xe lamp	1105	CO (41.02 $\mu\text{mol g}^{-1} \text{h}^{-1}$)	95	94% (5 cycles)	[153]
BiVO ₄ /Bi ₁₉ Cl ₃ S ₂₇	300 W Xe lamp	1152	CO (80.94 $\mu\text{mol g}^{-1} \text{h}^{-1}$)	96	95% (5 cycles)	[154]
CoFe ₂ O ₄ /BiVO ₄ /Bi ₂ WO ₆ /g-C ₃ N ₄ (This work)	300 W Xe lamp ($\lambda > 420 \text{ nm}$)	1300	CO (major), CH ₄ (minor)	98	94% (5 cycles)	This work

Mechanism Discussion

Energy Band Structure

The enhanced photocatalytic performance of the CoFe₂O₄/BiVO₄/Bi₂WO₆/g-C₃N₄ composite can be attributed to its well-designed direct Z-scheme energy band structure. The integration of narrow- and wide-band-gap semiconductors broadens visible-light absorption while maintaining strong redox capability. Under visible-light irradiation, each semiconductor absorbs photons according to its band-gap energy, generating electrons in the conduction band (CB) and holes in the valence band (VB). The favorable band alignment promotes efficient carrier separation and minimizes charge recombination. Consequently, highly reducing electrons and strongly oxidizing holes remain available for photocatalytic reactions, providing sufficient driving force for hydrogen production, CO₂ reduction, and degradation of organic contaminants.

The photocatalytic process follows a direct Z-scheme charge-transfer pathway. Upon light irradiation, electrons and holes are simultaneously generated in CoFe₂O₄, BiVO₄, Bi₂WO₆, and g-C₃N₄. Electrons possessing relatively weak reduction ability recombine with holes having lower oxidation ability at the heterojunction interfaces. This selective recombination effectively removes low-energy charge carriers while preserving highly energetic electrons and holes. As a result, electrons accumulate on the reduction-active semiconductor, whereas holes remain on the oxidation-active component. The intimate interfacial contact established during hydrothermal assembly shortens the migration distance of charge carriers and suppresses their bulk recombination. This efficient charge-transfer pathway is consistent with the reduced PL intensity, smaller EIS semicircle, and enhanced photocurrent response observed for the quaternary composite [150].

Charge Migration Pathway

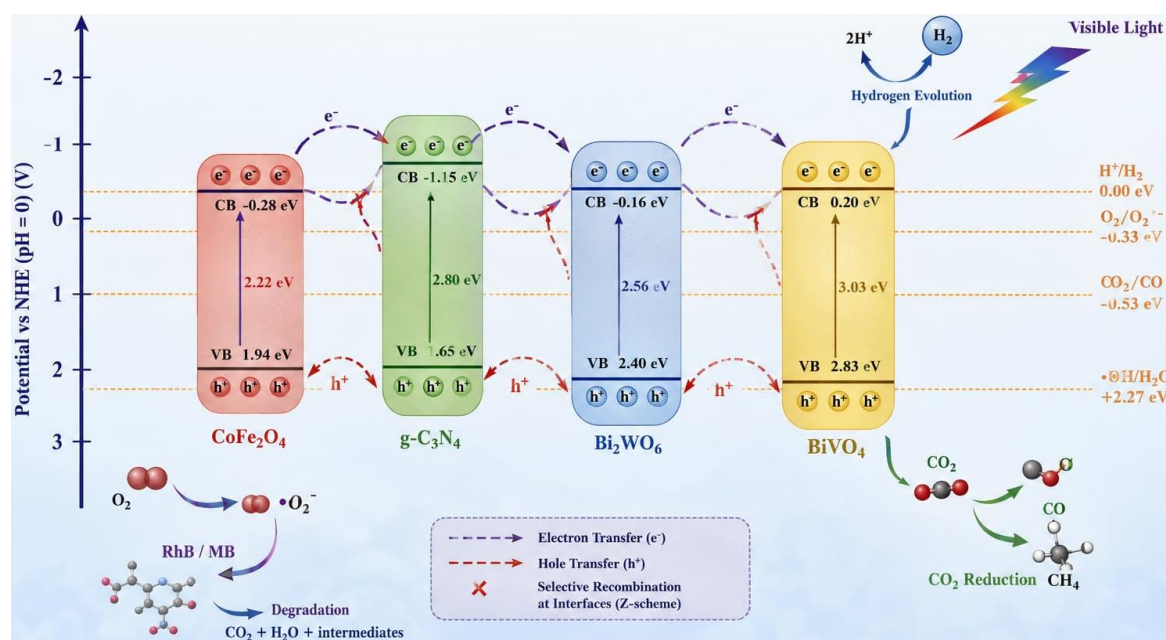


Figure 17: Proposed direct Z-scheme charge-transfer mechanism illustrating the energy band alignment, migration of photogenerated charge carriers, formation of reactive oxygen species, and the photocatalytic pathways for hydrogen evolution, CO₂ reduction, and organic pollutant degradation under visible-light irradiation

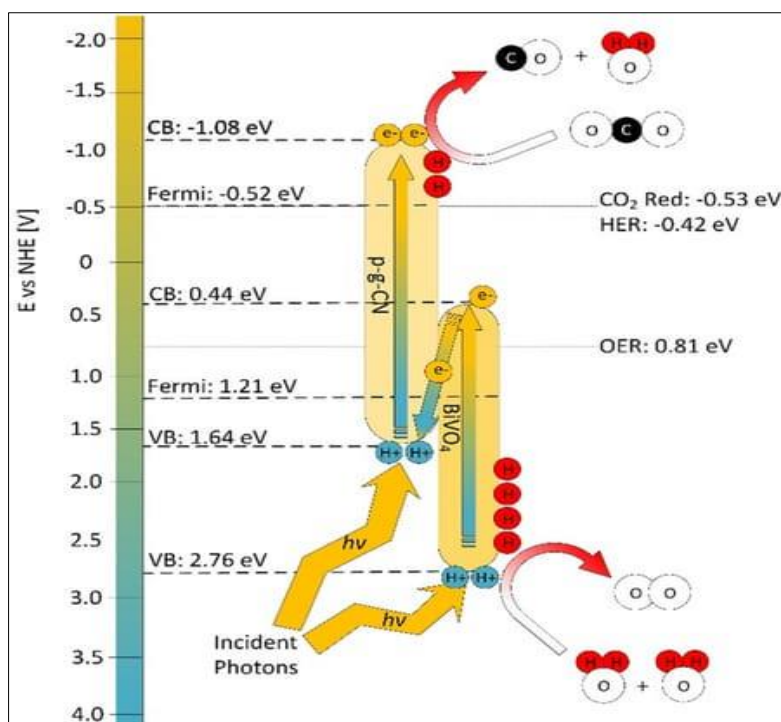


Figure 18: Energy Band Structure and Proposed Direct Z-Scheme Charge Transfer Mechanism of the $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ Photocatalyst

Generation of Reactive Oxygen Species

The preserved high-energy electrons react readily with dissolved oxygen to generate superoxide radicals ($\bullet\text{O}_2^-$), whereas the strongly oxidizing holes either directly oxidize organic molecules or react with surface hydroxyl groups and water to produce hydroxyl radicals ($\bullet\text{OH}$). These reactive oxygen species exhibit high oxidation potential and rapidly attack complex organic pollutants, converting them into smaller intermediates followed by complete mineralization. The radical trapping experiments confirmed that $\bullet\text{O}_2^-$ and $\bullet\text{OH}$ are the dominant reactive species, while photogenerated holes also contribute significantly to the oxidation process. The simultaneous generation of multiple reactive species greatly improves photocatalytic efficiency under visible-light irradiation.

CO_2 Reduction Mechanism

During CO_2 photoreduction, CO_2 molecules are first adsorbed onto the catalyst surface and activated at the available reaction sites. The photogenerated electrons with strong reduction potential participate in multi-electron transfer reactions, converting adsorbed CO_2 into valuable carbon-based products. In the present study, CO was identified as the primary reduction product, whereas CH_4 was formed as a secondary product through further electron and proton transfer steps. Efficient charge separation and prolonged carrier lifetime increase the probability of interfacial reduction reactions while suppressing undesirable recombination losses. The enlarged surface area of the composite further facilitates CO_2 adsorption and improves the overall conversion efficiency [155].

Hydrogen Evolution Mechanism

Hydrogen evolution proceeds through the reduction of adsorbed protons by photogenerated electrons accumulated at the reduction-active sites of the direct Z-scheme photocatalyst. The efficient migration of electrons across the heterojunction ensures a continuous supply of charge carriers for the hydrogen evolution reaction. Simultaneously, photogenerated holes are rapidly consumed in oxidation reactions, preventing electron accumulation and minimizing recombination. The combination of efficient visible-light harvesting, fast interfacial charge transfer, and abundant catalytic active sites enables the composite to achieve a hydrogen evolution rate of approximately $1300 \mu\text{mol h}^{-1} \text{g}^{-1}$, demonstrating its excellent potential for solar fuel production [157].

Organic Pollutant Degradation Mechanism

The degradation of Rhodamine B and Methylene Blue is initiated by the adsorption of dye molecules onto the catalyst surface. Under visible-light irradiation, the generated $\bullet\text{O}_2^-$, $\bullet\text{OH}$, and photogenerated holes attack the chromophoric structures of the pollutants, resulting in successive bond cleavage, ring-opening reactions, and oxidation of intermediate compounds. Continuous oxidation ultimately converts the organic molecules into CO_2 , H_2O , and other environmentally benign products, which is supported by the high mineralization efficiency obtained from TOC analysis. The hierarchical architecture of the $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ composite provides numerous active sites and facilitates rapid mass transfer,

enabling efficient interaction between reactive species and pollutant molecules. Consequently, the direct Z-scheme heterojunction simultaneously enhances charge separation, visible-light utilization, and photocatalytic reaction kinetics, leading to outstanding multifunctional photocatalytic performance [158].

Practical Significance and Future Perspectives

The multifunctional $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ photocatalyst demonstrates considerable potential for practical environmental and energy-related applications owing to its efficient visible-light response, excellent charge separation, and stable photocatalytic performance. The integration of four complementary semiconductor components enables simultaneous hydrogen evolution, CO_2 photoreduction, and degradation of organic pollutants, making the developed material a promising candidate for sustainable solar-driven technologies.

The photocatalyst also exhibits strong potential for solar fuel production. Its enhanced hydrogen evolution activity demonstrates the capability to convert abundant solar energy into clean hydrogen fuel. Simultaneously, the efficient reduction of CO_2 into valuable carbon-based products such as CO and CH_4 provides an attractive strategy for utilizing greenhouse gases while producing renewable chemical feedstocks. These dual functions support the development of integrated solar energy conversion technologies with reduced environmental impact [156].

From an industrial viewpoint, the hydrothermal synthesis strategy employed in this work is relatively simple, cost-effective, and reproducible, making it suitable for scale-up with appropriate process optimization. The use of visible light instead of ultraviolet radiation further improves energy efficiency and facilitates outdoor solar applications. The excellent structural stability and magnetic recoverability of the composite also enhance its suitability for repeated operation in industrial photocatalytic reactors.

Despite these advantages, several challenges remain before practical commercialization can be achieved. Large-scale synthesis with consistent product quality, long-term structural durability under real environmental conditions, and efficient utilization of natural sunlight require further investigation. The influence of complex wastewater matrices, catalyst fouling, and competing ions on photocatalytic performance should also be systematically evaluated. In addition, improving solar-to-hydrogen conversion efficiency, increasing CO_2 reduction selectivity toward higher-value hydrocarbons, and developing continuous-flow photocatalytic reactors remain important research directions. Future studies integrating advanced material engineering, theoretical calculations, and reactor design are expected to accelerate the practical implementation of multifunctional Z-scheme photocatalysts for

environmental remediation and sustainable energy production [159].

CONCLUSIONS

In this study, a novel $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ direct Z-scheme multi-heterojunction photocatalyst was successfully synthesized through an in-situ ultrasonication-assisted hydrothermal approach. The structural and physicochemical characterizations confirmed the successful integration of all constituent semiconductors without the formation of impurity phases. XRD, FESEM, TEM, EDX mapping, XPS, FTIR, and Raman analyses verified the high crystallinity, uniform elemental distribution, strong interfacial interaction, and preserved crystal structures of the individual components. UV-Vis DRS demonstrated enhanced visible-light absorption, while PL, EIS, photocurrent, and Mott-Schottky analyses confirmed efficient charge separation and rapid interfacial charge transfer through the direct Z-scheme pathway. The composite also exhibited a larger specific surface area and retained sufficient magnetic properties for convenient magnetic recovery after photocatalytic reactions. The developed photocatalyst exhibited outstanding multifunctional photocatalytic performance under visible-light irradiation. A hydrogen evolution rate of approximately $1300 \mu\text{mol h}^{-1} \text{g}^{-1}$ was achieved, demonstrating efficient solar-to-hydrogen conversion. During CO_2 photoreduction, CO was identified as the dominant product, whereas CH_4 was produced as a secondary reduction product, indicating effective utilization of photogenerated electrons for carbon conversion. The composite further achieved nearly 98% degradation of model organic pollutants together with an 88% mineralization efficiency, confirming the efficient removal of both dye molecules and their intermediate products. Radical trapping experiments revealed that $\bullet\text{O}_2^-$ and $\bullet\text{OH}$ radicals were the dominant reactive species, while photogenerated holes also contributed to the oxidation process. Moreover, the photocatalyst retained approximately 94% of its initial activity after five consecutive cycles without noticeable structural or morphological degradation, demonstrating excellent stability and recyclability. The superior photocatalytic activity can be attributed to the synergistic effect of the direct Z-scheme heterojunction. The intimate interfacial contact among CoFe_2O_4 , BiVO_4 , Bi_2WO_6 , and $\text{g-C}_3\text{N}_4$ effectively accelerated charge migration, suppressed electron-hole recombination, expanded visible-light absorption, and preserved strong oxidation and reduction potentials. These collective advantages significantly enhanced hydrogen evolution, CO_2 reduction, and organic pollutant degradation within a single multifunctional photocatalytic platform. The primary novelty of this work lies in the rational design of a quaternary direct Z-scheme photocatalyst capable of simultaneously addressing solar energy conversion, greenhouse gas utilization, and environmental remediation. Unlike conventional binary and ternary

heterojunctions, the present architecture integrates efficient charge separation, broad visible-light harvesting, abundant active sites, and magnetic recoverability within one stable material system. This multifunctional strategy provides an effective approach for overcoming the limitations of rapid charge recombination and insufficient solar-light utilization commonly encountered in conventional photocatalysts.

Key Takeaways

1. A novel $\text{CoFe}_2\text{O}_4/\text{BiVO}_4/\text{Bi}_2\text{WO}_6/\text{g-C}_3\text{N}_4$ direct Z-scheme multi-heterojunction photocatalyst was successfully developed through an in-situ ultrasonication-assisted hydrothermal strategy.
2. The quaternary heterojunction exhibited enhanced visible-light absorption, efficient charge separation, and rapid interfacial charge transfer, leading to superior photocatalytic performance.
3. The composite achieved a hydrogen evolution rate of approximately $1300 \mu\text{mol h}^{-1} \text{g}^{-1}$, while CO and CH_4 were obtained as the primary products during photocatalytic CO_2 reduction.
4. Nearly 98% degradation of model organic pollutants and 88% mineralization efficiency demonstrated the excellent environmental remediation capability of the developed photocatalyst.
5. The photocatalyst retained approximately 94% of its initial activity after five successive cycles, confirming its excellent stability, magnetic recoverability, and potential for practical solar fuel production and wastewater treatment applications.

REFERENCES

1. H. Kadkhodayan and T. Alizadeh, "Visible-light-driven CO_2 photoreduction to solar fuels over a Ni/Cu-loaded $\text{Bi}_2\text{ZnTiO}_6/\text{g-C}_3\text{N}_4$ 0D/3D/2D QDs Schottky/Z-scheme ternary heterojunction photocatalyst," Jun. 2026. <https://doi.org/10.1038/s41598-026-57310-x>
2. Iqbal, N., Bano, A., Ahmed, T., M.I. Nabeel, Ullah, J., Musharraf, S. G., & Malik, M. I. (2025). Fish gelatin nanoparticles: An effective carrier for curcumin delivery. *Journal of Drug Delivery Science and Technology*, 107505. <https://doi.org/10.1016/j.jddst.2025.107505>.
3. W. Chen, L. Ni, K. Ogino, H. Sun, and J. Bi, "Engineering $\text{g-C}_3\text{N}_4/\text{Bi}_2\text{WO}_6$ Composite Photocatalyst for Enhanced Photocatalytic CO_2 Reduction," Jan. 2025. <https://doi.org/10.3390/coatings15010032>
4. J. Chen, Y. Xiao, N. Wang, X. Kang, and D. Wang, "Facile synthesis of a Z-scheme $\text{CeO}_2/\text{C}_3\text{N}_4$ heterojunction with enhanced charge transfer for CO_2 photoreduction," May 2023. <https://doi.org/10.1007/s40843-023-2443-0>
5. N. Ahmad, S. Rasheed, A. Mohyuddin, B. Fatima, M.I. Nabeel, M.T. Riaz, M. Najam-ul-Haq, D. Hussain, 2D MXenes and their composites; design, synthesis, and environmental sensing applications, *Chemosphere* 352 (2024) 141280. <https://doi.org/https://doi.org/10.1016/j.chemosphere.2024.141280>.
6. Ali, M. A., Nabeel, M. I., Hussain, T., Awwad, A., Ismail, E. A., Mustafa, A., & Hassan, N. (2023). Radiation-induced degradation of PVA-26 by UV radiation in the presence of ZnO nanocatalyst. *J Biomed Res Environ Sci*, 4, 2276.
7. R. Mohamed, H. Abou Oualid, R. Eshaghi Malekshah, B. Ennasraoui, and H. Ighnih, "Efficient photocatalytic removal of ciprofloxacin antibiotic by dual Z-scheme $\text{Ag}_3\text{PO}_4/\text{g-C}_3\text{N}_4/\text{Bi}_2\text{WO}_6$ under solar irradiation," Jul. 2025. <https://doi.org/10.1016/j.jwpe.2025.108394>
8. Q. Xie, W. He, S. Liu, C. Li, and J. Zhang, "Bifunctional S-scheme $\text{g-C}_3\text{N}_4/\text{Bi}/\text{BiVO}_4$ hybrid photocatalysts toward artificial carbon cycling," Jan. 2020. [https://doi.org/10.1016/S1872-2067\(19\)63481-9](https://doi.org/10.1016/S1872-2067(19)63481-9)
9. M. Sayed, "Enhancing CO_2 photoreduction by construction of $\text{g-C}_3\text{N}_4/\text{Co-MOFs}$ S-scheme heterojunction," Feb. 2025. <https://doi.org/10.1016/j.apsusc.2025.162752>
10. Ather, N., Deh-ae, N., Khan, K., Nabeel, M. I., Qasim, M., Joseph, C. G., & Hussain, F. Microplastic Exposure, Oxidative Stress, and Potential Heme Protein Vulnerability in Teleost Fish: Implications for Oxygen Transport and Seafood Quality. *Frontiers in Environmental Science*, 14, 1904791.
11. M. Sabir, M. Sayed, S. Cao, *et al.*, "Enhancing CO_2 photoreduction by construction of $\text{g-C}_3\text{N}_4/\text{Co-MOFs}$ S-scheme heterojunction," Feb. 2025.
12. H. Kadkhodayan and T. Alizadeh, "Interfacial engineering of Ni/Cu-Loaded $\text{A}2\text{ZnTiO}_6/\text{X}$ -doped $\text{g-C}_3\text{N}_4$ schottky-contact Z-scheme heterojunction for enhanced visible-light-driven CO_2 photoreduction," Mar. 2026. <https://doi.org/10.1007/s10853-026-12582-6>
13. M. Ismail, M. Z. H. Makmud, and H. A. Illias, "Multifunctional surface coatings for photovoltaic modules: Anti-soiling, hydrophilic/phobic, and thermal management," *IEEE Access*, Mar. 2026. <https://doi.org/10.1109/ACCESS.2026.3674089>
14. M.I. Nabeel, Gulzar, T., Kiran, S., Ahmad, N., Raza, S. A., Batool, U., & Rehan, Z. A. (2025). Tailoring Graphitic Carbon Nitride ($\text{g-C}_3\text{N}_4$) for Multifunctional Applications: Strategies for Overcoming Challenges in Catalysis and Energy Conversion. *International Journal of Energy Research*, 2025(1), 5599894. <https://doi.org/10.1155/er/5599894>.
15. M.I. Nabeel, D. Hussain, N. Ahmad, M. Najam-ul-Haq, S.G. Musharraf, Recent advancements in the fabrication and photocatalytic applications of graphitic carbon nitride-tungsten oxide

- nanocomposites, *Nanoscale Advances* 5(19) (2023) 5214-5255. <https://doi.org/10.1039/D3NA00159H>.
16. J. Zhao, M. Ji, H. Chen, Y.-X. Weng, and J. Zhong, "Interfacial chemical bond modulated Bi₁₉S₂₇Br₃/g-C₃N₄ Z-scheme heterojunction for enhanced photocatalytic CO₂ conversion," Feb. 2022. <https://doi.org/10.1016/j.apcatb.2022.121162>
 17. N. T. T. Truc, T.-D. Pham, M. V. Nguyen, D. V. Thuan, and D. Q. Trung, "Advanced NiMoO₄/g-C₃N₄ Z-scheme heterojunction photocatalyst for efficient conversion of CO₂ to valuable products," Jun. 2020. <https://doi.org/10.1016/j.jallcom.2020.155860>
 18. L. Guo, Y. You, H. Huang, N. Tian, and T. Ma, "Z-scheme g-C₃N₄/Bi₂O₂[BO₂(OH)] heterojunction for enhanced photocatalytic CO₂ reduction," Feb. 2020. <https://doi.org/10.1016/j.jcis.2020.02.025>
 19. F. W. Ahmad, N. Ahmad, S. Rasheed, M.I. Nabeel, A. Mohyuddin, M.T. Riaz, D. Hussain, Silica-Based Superhydrophobic and Superoleophilic Cotton Fabric with Enhanced Self-Cleaning Properties for Oil-Water Separation and Methylene Blue Degradation, *Langmuir* 40(11) (2024) 5639-5650. <https://doi.org/10.1021/acs.langmuir.3c02821>.
 20. J. Li, Y. Ma, Y. Xu, P. Li, and J. Guo, "Enhanced photocatalytic degradation activity of Z-scheme heterojunction BiVO₄/Cu/g-C₃N₄ under visible light irradiation," Apr. 2021. <https://doi.org/10.1002/wer.1572>
 21. Ali, T., Ahmad, N., M. I. Nabeel, Xiao, H. M., & Hussain, D. (2024). Facile and Scalable Growth of Bimetallic 3D Ag/MIL125-NH₂ on Cotton Fabric for Multifaceted Anti-Wetting and Self-Healing Characteristics, *Carbon*, 119395. <https://doi.org/10.1016/j.carbon.2024.119395>.
 22. S. Bellamkonda, C. Chakma, S. Guru, B. Neppolian, G. Ranga Rao, *et al.*, "Rational design of plasmonic Ag@CoFe₂O₄/g-C₃N₄ p-n heterojunction photocatalysts for efficient overall water splitting," May 2022. <https://doi.org/10.1016/j.ijhydene.2022.04.059>
 23. Ibrahim, M. N. A., Joseph, C. G., Surugau, N., Nabeel, M. I., & Ismail, S. S. (2025). From waste to water cleanup: Preliminary study on sargassum-derived activated carbon (AC) for pollutant adsorption. *Mater. Emerg. Technol. Sustain*, 1, 2550015.
 24. M.I. Nabeel, D. Hussain, N. Ahmad, H.-M. Xiao, S.G. Musharraf, improved visible light-driven photocatalytic degradation of an industrial dye Acid Orange 7 using metal-free sulfur-doped graphitic carbon nitride, *Environmental Science: Nano* 10(10) (2023) 2810-2830. <https://doi.org/10.1039/D3EN00289F>.
 25. Q. Zhang, M. Liu, S. Liu, L. Qiao, and X. Hu, "Z-scheme g-C₃N₄/BiVO₄ photocatalysts with RGO as electron transport accelerator," Jan. 2020. <https://doi.org/10.1007/s10854-019-02573-6>
 26. M. J. Molaei, "Z-Scheme Heterojunction Photocatalysts: Principles, Engineering Strategies, and Applications in Solar-Driven Energy Conversion and Environmental Remediation," Jul. 2026. <https://doi.org/10.1002/jccs.70246>
 27. M. Lu, Q. Li, C. Zhang, X. Fan, L. Li, *et al.*, "Remarkable photocatalytic activity enhancement of CO₂ conversion over 2D/2D g-C₃N₄/BiVO₄ Z-scheme heterojunction promoted by efficient interfacial charge transfer," Apr. 2020. <https://doi.org/10.1016/j.carbon.2020.01.038>
 28. Y. Baghdadi, M. Daboczi, F. Temerov, M. Yang, and J. Cui, "A g-C₃N₄/rGO/Cs₃Bi₂Br₉ mediated Z-scheme heterojunction for enhanced photocatalytic CO₂ reduction," May 2024. <https://doi.org/10.1039/D4TA01857E>
 29. F. A. Qaraah, S. A. Mahyoub, Q. A. Drmosh, A. Qaraah, and F. Xin, "One-step fabrication of unique 3D/2D S, O-doped g-C₃N₄ S-scheme isotype heterojunction for boosting CO₂ photoreduction," Jun. 2023. <https://doi.org/10.1016/j.mtsust.2023.100437>
 30. X. Li, J. Guan, H. Jiang, X. Song, and P. Huo, "rGO modified R-CeO₂/g-C₃N₄ multi-interface contact S-scheme photocatalyst for efficient CO₂ photoreduction," Jun. 2021. <https://doi.org/10.1016/j.apsusc.2021.150042>
 31. W.-K. Jo, S. Kumar, S. Eslava, and S. Tonda, "Construction of Bi₂WO₆/RGO/g-C₃N₄ 2D/2D/2D hybrid Z-scheme heterojunctions with large interfacial contact area for efficient charge separation and high-performance photoreduction of CO₂ and H₂O into solar fuels," Aug. 2018. <https://doi.org/10.1016/j.apcatb.2018.08.056>
 32. Qasim, M., Manzoor, S., Nabeel, M. I., Hussain, S., Waqas, R., Joseph, C. G., & Suazo-Hernández, J. (2025). Harnessing High-Valent Metals for Catalytic Oxidation: Next-Gen Strategies in Water Remediation and Circular Chemistry. *Catalysts*, 15(12), 1168. <https://doi.org/10.3390/catal15121168>.
 33. Q. Yao, P. Liu, F. Yang, Y. Zhu, and Y. Pan, "Ferroelectric polarization in Bi_{0.9}Dy_{0.1}FeO₃/g-C₃N₄ Z-scheme heterojunction boosts photocatalytic hydrogen evolution," Aug. 2024. <https://doi.org/10.1007/s40843-024-3036-y>
 34. Q. Wang, Y. Lin, P. Li, M. Ma, and V. Maheskumar, "An efficient Z-scheme (Cr, B) codoped g-C₃N₄/BiVO₄ photocatalyst for water splitting: A hybrid DFT study," Oct. 2020. <https://doi.org/10.1016/j.ijhydene.2020.09.252>
 35. M.I. Nabeel, Hussain, D., Ahmad, N., Xiao, H. M., Ahmad, W., & Musharraf, S. G. (2025). Facile one-pot synthesis of metal and non-metal doped g-C₃N₄ photocatalyst for rapid acetaminophen remediation. *Carbon*, 120472. <https://doi.org/10.1016/j.carbon.2025.120472>.
 36. Kiran, S., Gulzar, T., Ijaz, M. U., Sethi, A., Nadeem, L., Yousaf, A., ... & Nabeel, M. I. (2026). Sonochemical technology in the degradation of textile dye effluents. In *Sonochemistry for Textile*

- and Fibre Engineering (pp. 193-215). Woodhead Publishing.
37. R. Song, S. Kang, L. Yao, L. Zheng, and D. Yu, "Construction of an La-BiVO₄/O-Doped g-C₃N₄ Heterojunction Photocatalyst Embedded in Electrospinning Nanofibers," May 2023. <https://doi.org/10.1021/acs.langmuir.2c03356>
 38. L. Pei, Z. Luo, X. Wang, Z. Ma, and Y. Nie, *et al.*, "Tunable CO₂-to-Syngas Conversion via Strong Electronic Coupling in S-scheme ZnGa₂O₄/g-C₃N₄ Photocatalysts," Jul. 2023. <https://doi.org/10.1016/j.jcis.2023.07.148>
 39. M.I. Nabeel, Ahmad, N., Arif, S., Hussain, D., & Musharraf, S. G. (2025). Facile Two-Step Synthesis of Yttrium-Doped g-C₃N₄ for Enhanced Photocatalytic Degradation of Methylene Blue with Self-Cleaning Properties. *Nanoscale Advances*. <https://doi.org/10.1039/D5NA00600G>.
 40. Ullah, Z., Joseph, C. G., Tian, Z. Y., Yasin, M., Khan, M. N., Ali, S., ... & M. I. Nabeel, (2025). The Production of Biochar and Its Impact on the Removal of Various Emerging Pollutants from Wastewater: A Review. *Toxics*, 13(12), 1079 <https://doi.org/10.3390/toxics13121079>.
 41. T. Liu, Y. Wu, H. Wang, J. Lu, and Y. Luo, "Defect-Engineered Z-Scheme Heterojunction of Fe-MOFs/Bi₂WO₆ for Solar-Driven CO₂ Conversion: Synergistic Surface Catalysis and Interfacial Charge Dynamics," Apr. 2025. <https://doi.org/10.3390/nano15080618>
 42. X. Zhang, K. Matras-Postolek, P. Yang, and S. P. Jiang, *et al.*, "Z-Scheme WO_x/Cu-g-C₃N₄ Heterojunction Nanoarchitectonics with Promoted Charge Separation and Transfer towards Efficient Full Solar-Spectrum Photocatalysis," Jan. 2023. <https://doi.org/10.1016/j.jcis.2023.01.052>
 43. Y. Xu, J. Yu, J. Long, L. Tu, and W. Dai, *et al.*, "Z-Scheme Heterojunction of SnS₂/Bi₂WO₆ for Photoreduction of CO₂ to 100% Alcohol Products by Promoting the Separation of Photogenerated Charges," Jun. 2022. <https://doi.org/10.3390/nano12122030>
 44. X. Yin, X. Sun, D. Li, W. Xie, and Y. Mao, *et al.*, "2D/2D Phosphorus-Doped g-C₃N₄/Bi₂WO₆ Direct Z-Scheme Heterojunction Photocatalytic System for Tetracycline Hydrochloride (TC-HCl) Degradation," Nov. 2022. <https://doi.org/10.3390/ijerph192214935>
 45. Shahzad, F., Hussain, E., Nadeem, N., Nabeel, M. I., Saeed, M., Joseph, C. G., ... & Sajid, M. (2026). GREEN SYNTHESIS OF COPPER OXIDE NANOPARTICLES TO HARVEST THE LIGHT FOR PHOTOCATALYTIC DEGRADATION OF DYES METHYLENE BLUE AND METHYL ORANGE. *Borneo Science| The Journal of Science and Technology*, 47(1). <https://doi.org/10.51200/bsj.v47i1.7565>
 46. Gulzar, T., Ullah, H., Maqsood, A., Abrar, S., Nabeel, M. I., Kanwal, A., & Raza, S. A. (2025). Panoramic View of Biomedical Textiles and Their Synthetic Strategies. In *Biomedical Textiles* (pp. 1-34). Jenny Stanford Publishing.
 47. J. Qin, M. Zhao, Y. Zhang, J. Shen, and X. Wang, "Probing Local Structure and Electronic Structure of A-Fe₂O₃/G-C₃N₄ S-Scheme Heterojunctions for Boosting Co₂ Photoreduction," Jan. 2024. <https://doi.org/10.2139/ssrn.4909247>
 48. Y. Zhang, N. Nwaji, L. Wu, M. Jin, and J. Lee, *et al.*, "MAPbBr₃/Bi₂WO₆ Z-scheme-heterojunction photocatalysts for photocatalytic CO₂ reduction," Jan. 2024. <https://doi.org/10.1007/s10853-023-09220-w>
 49. M.I.Nabeel, D.Hussain, S.G. Musharraf, N. Ahmad, Advanced Doped and Composite Graphitic Carbon Nitride Photocatalysts for Efficient Degradation of Organic Pollutants under Visible Light, in *Proceedings of The 1st International Online Conference on Xenobiotics*, 22 June–23 June 2026, MDPI: Basel, Switzerland
 50. R. LaChance, B. Adeli, and F. Taghipour, "Solar Fuel Generation by 2D Self-Assembled g-C₃N₄/BiVO₄ Z-Scheme," Dec. 2023. <https://doi.org/10.1002/solr.202300677>
 51. H. Xie, Y. Zhao, H. Li, Y. Xu, and X. Chen, "2D BiVO₄/g-C₃N₄ Z-scheme photocatalyst for enhanced overall water splitting," Aug. 2019. <https://doi.org/10.1007/s10853-019-03664-9>
 52. K. Wu, S. Song, H. Wu, J. Guo, L. Zhang, *et al.*, "Facile synthesis of Bi₂WO₆/C₃N₄/Ti₃C₂ composite as Z-scheme photocatalyst for efficient ciprofloxacin degradation and H₂ production," Nov. 2020. <https://doi.org/10.1016/j.apcata.2020.117869>
 53. M.I. Nabeel., Hussain, D., Ahmad, N., Saeed, A., Ali, K., Xiao, H. M., & Musharraf, S. G. (2025). Facile Synthesis of Robust 2D Z-scheme Ultrathin Sulfur Doped g-C₃N₄-Tungsten Oxide Composite by High Pressure Vacuum Filtration for 5-FU Detoxification. *Surfaces and Interfaces*, 108278. <https://doi.org/10.1016/j.surfin.2025.108278>.
 54. C. Zhang, R. Li, Y. Zhao, and M. Wang, "Construction of Z-Scheme Bi₂WO₆/g-C₃N₄ Heterojunction Photocatalysts with Enhanced Visible-Light Photocatalytic Activity," Apr. 2017. <https://doi.org/10.1071/CH16507>
 55. P. Mane, H. Bae, V. Burungale, S.-W. Lee, and M. Misra, "Interface-engineered Z-scheme of BiVO₄/g-C₃N₄ photoanode for boosted photoelectrochemical water splitting and organic contaminant elimination under solar light," Aug. 2022. <https://doi.org/10.1016/j.chemosphere.2022.136166>
 56. Arif, S., Rasheed, S., Ahmad, N., M. I. Nabeel, Ahmad, W., Alomayri, T., ... & Musharraf, S. G. (2026). Carbon-based materials for photocatalytic degradation of pharmaceuticals and drugs. *Journal of Water Process Engineering*, 81, 109274 <https://doi.org/10.1016/j.jwpe.2025.109274>.
 57. Y. Feng, D. Chen, Y. Zhong, Z. He, and S. Ma, *et al.*, "A Lead-Free 0D/2D Cs₃Bi₂Br₉/Bi₂WO₆ S-

- Scheme Heterojunction for Efficient Photoreduction of CO₂,” Feb. 2023. <https://doi.org/10.1021/acsami.2c19703>
58. M. Sabir, M. Sayed, I. Riaz, G. Qiu, and M. Tahir, “Ni-MOF/g-C₃N₄ S-Scheme Heterojunction for Efficient Photocatalytic CO₂ Reduction,” Jul. 2025. <https://doi.org/10.3390/ma18143419>
 59. Z. Wei, F. Yue, H. Haibao, Z. Pengcheng, and L. Jing, “A novel Z-scheme Ag₃VO₄/BiVO₄ heterojunction photocatalyst: Study on the excellent photocatalytic performance and photocatalytic mechanism,” May 2019. <https://doi.org/10.1016/j.apcatb.2019.01.001>
 60. Raza, H. Shen, A. A. Haidry, *et al.*, “Novel Cu₂ZnSnS₄/Pt/g-C₃N₄ heterojunction photocatalyst with straddling band configuration for enhanced solar to fuel conversion,” Nov. 2020. <https://doi.org/10.1016/j.apcatb.2020.119239>
 61. Y. Peng, P.-Y. Dugas, K. C. Szeto, C. C. Santini, S. Daniele, *et al.*, “Interplay Between Ionic Liquids, Kolbe Chemistry, and 2D Photocatalyst Supports in Aqueous CO₂ Photoreduction over Pd/TiO₂ and Pd/g-C₃N₄,” Dec. 2025. <https://doi.org/10.3390/catal15121128>
 62. G. Rana, R. Verma, E. A. Alabdulkarem, S. K. Rao, and K.-Y. A. Lin, “Z-Scheme CoFe₂O₄/g-C₃N₄/MWCNT catalyst for the degradation of organic pollutants: electrochemical evaluation and HPLC analysis of the intermediates,” Jun. 2026. <https://doi.org/10.1039/d6ra02055k>
 63. R. Zhang and K. Zeng, “A novel flower-like dual Z-scheme BiSI/Bi₂WO₆/g-C₃N₄ photocatalyst has excellent photocatalytic activity for the degradation of organic pollutants under visible light,” Mar. 2021. <https://doi.org/10.1016/j.diamond.2021.108343>
 64. Z. Zhai, J. Bi, L. Wang, N. Liu, Y. Wang, *et al.*, “Synergistic Photocatalytic Removal of U(VI) and Tetracycline over a Dual Z-scheme g-C₃N₄/Bi₂MoO₆/Bi₂WO₆ Heterojunction,” Jan. 2026. <https://doi.org/10.2139/ssrn.6777198>
 65. Z. Zhang, D. Zhang, L. Lyu, G. Cui, and H. Lu, “In Situ Formation of Z-Scheme Bi₂WO₆/WO₃ Heterojunctions for Gas-Phase CO₂ Photoreduction with H₂O by Photohydrothermal Treatment,” Oct. 2022. <https://doi.org/10.3390/catal12101237>
 66. R. Sun, Q. Shi, M. Zhang, L. Xie, and J. Chen, “Enhanced photocatalytic oxidation of toluene with a coral-like direct Z-scheme BiVO₄/g-C₃N₄ photocatalyst,” Apr. 2017. <https://doi.org/10.1016/j.jallcom.2017.04.108>
 67. P. Zhu, S. Zhang, R. Liu, D. Luo, and H. Yao, “Investigation of an enhanced Z-scheme magnetic recyclable BiVO₄/GO/CoFe₂O₄ photocatalyst with visible-light-driven for highly efficient degradation of antibiotics,” Jul. 2022. <https://doi.org/10.1016/j.jssc.2022.123379>
 68. Y. Baghdadi, F. Temerov, J. Cui, M. Daboczi, and E. Rattner, “Cs₃Bi₂Br₉/g-C₃N₄ Direct Z-Scheme Heterojunction for Enhanced Photocatalytic Reduction of CO₂ to CO,” Oct. 2023. <https://doi.org/10.1021/acs.chemmater.3c01635>
 69. P. Sang and J. H. Kim, “Role of g-C₃N₄ in Fabrication of BiVO₄/WO₃ Z-scheme Heterojunction for high Photoelectrochemical Performances with Enhanced Light Harvesting,” Oct. 2022. <https://doi.org/10.1007/s40684-022-00478-0>
 70. Z. Zhao, J. Bian, L. Zhao, H. Wu, and S. Xu, “Construction of 2D Zn-MOF/BiVO₄ S-scheme heterojunction for efficient photocatalytic CO₂ conversion under visible light irradiation,” May 2022. [https://doi.org/10.1016/S1872-2067\(21\)64005-6](https://doi.org/10.1016/S1872-2067(21)64005-6)
 71. P. Sang and J. H. Kim, “Role of g-C₃N₄ in Fabrication of BiVO₄/WO₃ Z-scheme Heterojunction for high Photoelectrochemical Performances with Enhanced Light Harvesting,” Oct. 2022. <https://doi.org/10.1007/s40684-022-00478-0>
 72. J. Ren, Q. Ma, X. Sun, S.-F. Wang, and G. Liu, “Interface-engineering enhanced photocatalytic conversion of CO₂ into solar fuels over S-type Co-Bi₂WO₆@Ce-MOF heterostructured photocatalysts,” Mar. 2025. <https://doi.org/10.1016/j.jcis.2025.137452>
 73. Z. Wang, R. Liu, J. Zhang, and K. Dai, “S-scheme Porous g-C₃N₄/Ag₂MoO₄ Heterojunction Composite for CO₂ Photoreduction,” Jun. 2022. <https://doi.org/10.14102/j.cnki.0254-5861.2022-0108>
 74. W. Ali, F. Ali, W. Muhammad, M. Z. Ansar, and Z. U. Khan, “Construction of 2D/2D α-Fe₂O₃/g-C₃N₄ Z-scheme photocatalysts with SnO₂ as an energy platform for directed charge transfer in cascade heterojunction: Photocatalytic CO₂ reduction and pollutant degradation,” Mar. 2025. <https://doi.org/10.1016/j.jcis.2025.137459>
 75. D. Kim and K. Yong, “Boron doping induced charge transfer switching of a C₃N₄/ZnO photocatalyst from Z-scheme to type II to enhance photocatalytic hydrogen production,” Mar. 2021. <https://doi.org/10.1016/j.apcatb.2020.119538>
 76. L. Jiang, H. Du, L. Li, X. Guan, and Y. Zhang, “Sequential Growth of Cs₃Bi₂I₉/BiVO₄ Direct Z-Scheme Heterojunction for Visible-Light-Driven Photocatalytic CO₂ Reduction,” Dec. 2023. <https://doi.org/10.1007/s12209-023-00376-9>
 77. B. Ma, Y. Zha, P. Yu, G. Chen, and Y. Guo, “Hydrothermal nanoarchitectonics of Z-scheme g-C₃N₄/Bi₂WO₆ heterojunction with enhanced adsorption and photocatalytic activity for fluoroquinolone antibiotics removal: Kinetics, mechanism and degradation pathway,” Apr. 2023. <https://doi.org/10.1016/j.jallcom.2023.170061>
 78. Y. Li, Z. Xia, Q. Yang, L. Wang, Y. Xing, *et al.*, “Review on g-C₃N₄-based S-scheme Heterojunction Photocatalysts,” Apr. 2022. <https://doi.org/10.1016/j.jmst.2022.02.035>

79. S. Tang, Y. Ma, H. Wang, Y. Liang, and X. Xu, "One-Pot Synthesis of 2D-2D WO₃/g-C₃N₄ Photocatalyst in Reverse Microemulsion System via Supercritical CO₂ for Enhanced Hydrogen Generation," Apr. 2023. <https://doi.org/10.1002/cssc.202202184>
80. P. Zhu, D. Luo, M. Liu, M. Duan, J. Lin, *et al.*, "Flower-globular BiOI/BiVO₄/g-C₃N₄ with a dual Z-scheme heterojunction for highly efficient degradation of antibiotics under visible light," Jun. 2022. <https://doi.org/10.1016/j.seppur.2022.121503>
81. Q. Chen, J. Huang, D. Chu, L. Cao, and X. Li, "Accelerated Photogenerated Charge Separation Driven Synergistically by the Interfacial Electric Field and Work Function in Z-Scheme Zn-Ni₂P/G-C₃N₄ for Efficient Photocatalytic Hydrogen Evolution," Aug. 2025. <https://doi.org/10.1002/EXP.20240189>
82. Z. Duan, X. Zhao, L. Chen, *et al.*, "BiVO₄/Cu_{0.4}V₂O₅ composites as a novel Z-scheme photocatalyst for visible-light-driven CO₂ conversion," Oct. 2020. <https://doi.org/10.1016/j.jece.2020.104628>
83. Y. Bai, Z. Chen, D. Gu, R. Wang, and J. He, "Modification of AgInS₂/g-C₃N₄ Z-Scheme Heterojunction by Ag Nanoparticles to Increase Photocatalytic Rate," Apr. 2025. <https://doi.org/10.1007/s10562-025-04975-0>
84. C. Yang, Q. Zhang, W. Wang, B. Cheng, and J. Yu, "2D/2D g-C₃N₄@BiOI S-scheme heterojunction with gas-liquid-solid triphase interface for highly efficient CO₂ photoreduction," Apr. 2024. <https://doi.org/10.1007/s40843-024-2789-0>
85. L. Gaozong, S. Xie, H. Peng, H. Huang, H. Ning, *et al.*, "Study on Photocatalytic Oxidation of MG and reduction of Cr (VI) by Sulfur-doped g-C₃N₄/Bi₂WO₆ tungstate Z-type heterojunction under LED Light source irradiation," Jan. 2026. <https://doi.org/10.2139/ssrn.6439371>
86. G. Gebreslassie, M. Gebrezgiabher, B. Lin, M. Thomas, and W. Linert, *et al.*, "Direct Z-Scheme CoFe₂O₄-Loaded g-C₃N₄ Photocatalyst with High Degradation Efficiency of Methylene Blue under Visible-Light Irradiation," Mar. 2023. <https://doi.org/10.3390/inorganics11030119>
87. M. H. Aziz, M. Asif, M. Fatima, M. T. Khan, and A. F. El-kott, *et al.*, "Synergistic impact of CoFe₂O₄/g-C₃N₄/WO₃ as dual Z-scheme photocatalyst for improving tetracycline (TC-HCl) degradation and antibacterial performance," Apr. 2026. <https://doi.org/10.1007/s10853-026-12645-8>
88. M. Sayed, B. Zhu, P. Kuang, X. Liu, and B. Cheng, *et al.*, "EPR Investigation on Electron Transfer of 2D/3D g-C₃N₄/ZnO S-Scheme Heterojunction for Enhanced CO₂ Photoreduction," Oct. 2021. <https://doi.org/10.1002/adsu.202100264>
89. H. Ren, X. Sun, T. Li, Z. Ren, and C. Song, "Preparation of a Z-scheme BiVO₄/Cu₂O/PPy heterojunction and studying its CO₂ reducing properties," Apr. 2025. <https://doi.org/10.1039/d4ra08130g>
90. J. Jia, Q. Zhang, K. Li, Y. Zhang, and E. Liu, "Recent advances on g-C₃N₄-based Z-scheme photocatalysts: Structural design and photocatalytic applications," Oct. 2022. <https://doi.org/10.1016/j.ijhydene.2022.09.272>
91. N. Madima, K. K. Kefeni, A. T. Kuvarega, S. B. Mishra, and A. K. Mishra, *et al.*, "Visible-light-driven Z-scheme ternary Fe₃O₄/TiO₂/g-C₃N₄ nanocomposite as reusable photocatalyst for efficient removal of dyes and chromium in water," Dec. 2022. <https://doi.org/10.1016/j.matchemphys.2022.127233>
92. I.-H. Tsai, C.-H. Fu, T.-H. Lin, S.-Y. Lin, and E. W.-G. Diao, "Enhanced Photocatalytic Performance for CO₂ Reduction Using an Indirect Z-Scheme Heterojunction Photocatalyst," May 2026. <https://doi.org/10.1002/cssc.70716>
93. J. Wu, K. Li, S. Yang, C. Song, and X. Guo, "In-situ construction of BiOBr/Bi₂WO₆ S-scheme heterojunction nanoflowers for highly efficient CO₂ photoreduction: Regulation of morphology and surface oxygen vacancy," Sep. 2022. <https://doi.org/10.1016/j.ccej.2022.139493>
94. M. Osemba, "Vacancy-Regulated Dual Single-Atom COF/g-C₃N₄ S-Scheme Heterostructures for Selective Multi-Carbon Product Formation via Solar-Driven Artificial Photosynthesis," Jul. 2026. <https://doi.org/10.26434/chemrxiv.15005969/v1>
95. C. Luo, Q. Long, B. Cheng, B. Zhu, and L. Wang, "A DFT Study on S-Scheme Heterojunction Consisting of Pt Single Atom Loaded G-C₃N₄ and BiOCl for Photocatalytic CO₂ Reduction," Jun. 2023. <https://doi.org/10.3866/PKU.WHXB202212026>
96. Z. Tang, C. Wang, W. He, Y. Wei, and Z. Zhao, "The Z-scheme g-C₃N₄/3DOM-WO₃ photocatalysts with enhanced activity for CO₂ photoreduction into CO," Jul. 2021. <https://doi.org/10.1016/j.cclet.2021.07.020>
97. J. Geng, S. Guo, Z. Zou, Z. Yuan, and D. Zhang, "0D/2D CeO₂/BiVO₄ S-scheme photocatalyst for production of solar fuels from CO₂," Feb. 2023. <https://doi.org/10.1016/j.fuel.2022.126417>
98. G. Wang, Z. Luo, Q. Wei, C. Peng, and Q. Liu, "Dual-metal sites CuInS₂/g-C₃N₄ Z-scheme heterojunction with efficient photocatalytic CO₂ reduction selectivity," Dec. 2022. <https://doi.org/10.1016/j.fuproc.2022.107530>
99. Y. Yang, J. Wu, T. Xiao, Z. Tang, and J. Shen, "Urchin-like hierarchical CoZnAl-LDH/RGO/g-C₃N₄ hybrid as a Z-scheme photocatalyst for efficient and selective CO₂ reduction," May 2019. <https://doi.org/10.1016/j.apcatb.2019.117771>
100. B. Palanivel, M. Lallimathi, B. Arjunkumar, M. Shkir, and T. Alshahrani, *et al.*, "rGO supported g-C₃N₄/CoFe₂O₄ heterojunction: Visible-light-active photocatalyst for effective utilization of

- H₂O₂ to organic pollutant degradation and OH• radicals production,” Nov. 2020. <https://doi.org/10.1016/j.jece.2020.104698>
101. M. Dong, S. Yang, P. Zhou, Z. Huang, and S. Tu, *et al.*, “UiO-66-mediated Bi₂WO₆/AgI heterojunction photocatalyst for efficient visible-light-driven tetracycline degradation,” Jul. 2026. <https://doi.org/10.1007/s10853-026-13211-y>
 102. Z. Zhu, C. Ma, K. Yu, Z. Lu, and Z. Liu, “Fabrication of CoFe₂O₄-modified and HNTs-supported g-C₃N₄ heterojunction photocatalysts for enhancing MBT degradation activity under visible light,” Apr. 2020. <https://doi.org/10.1007/s10853-019-04170-8>
 103. S. Tahir, Z. A. Rehan, M. S. Khan, G. Mustafa, and S. Noreen, “Design, synthesis and characterization of g-C₃N₄/GO/CoFe₂O₄ nanocomposite for efficient photocatalytic degradation of pollutants using sunlight,” May 2026. <https://doi.org/10.1007/s13762-026-07252-8>
 104. Q. Li, L. Li, X. Long, Y. Tu, and L. Ling, “Rational design of MIL-88A(Fe)/Bi₂WO₆ heterojunctions as an efficient photocatalyst for organic pollutant degradation under visible light irradiation,” Aug. 2021. <https://doi.org/10.1016/j.optmat.2021.111260>
 105. Gulzar, T., Sethi, A., Maqsood, A., Batool, U., Maqsood, N., Raza, S. A., & Nabeel, M. I. (2025). Developmental Vistas for Bioactive Textile Engineering. In Biomedical Textiles (pp. 133-166). Jenny Stanford Publishing.
 106. O. T. K. Nguyen, T. V. Huynh, B. G. Tran, H. Q. Ha, V. H. Nguyen, and Q.-M. T. Doan, “Synthesis of BiVO₄/g-C₃N₄ heterojunction photocatalyst for enhanced doxycycline degradation under LED light illumination,” Jan. 2026. <https://doi.org/10.1016/j.mseb.2025.118804>
 107. G. Abimannan, “BiVO₄/g-C₃N₄ as an efficient photocatalyst for degradation of organic pollutants,” Conference Paper, Mar. 2023.
 108. J. Li, Y. Ma, Y. Xu, P. Li, and J. Guo, “Enhanced photocatalytic degradation activity of Z-scheme heterojunction BiVO₄/Cu/g-C₃N₄ under visible light irradiation,” Apr. 2021. <https://doi.org/10.1002/wer.1572>
 109. T. H. T. Vu, N. Q. T. Ton, and T. G. B. Nguyen, “Construction of SrTiO₃/g-C₃N₄ Heterojunction for Improved Visible-Light-Driven Photocatalytic Activity toward Decomposition of Organic Pollutants in Water,” Sep. 2025. <https://doi.org/10.32508/stdj.v28i3.4465>
 110. J. Zhao, J. Yan, H. Jia, S. Zhong, and X. Zhang, *et al.*, “BiVO₄/g-C₃N₄ composite visible-light photocatalyst for effective elimination of aqueous organic pollutants,” Aug. 2016. <https://doi.org/10.1016/j.molcata.2016.08.025>
 111. B. Rabeie, N. M. Mahmoodi, and H. Kazemian, “Visible light assisted magnetic COF/HKUST/CoFe₂O₄ composite as a novel photocatalyst: green synthesis and efficient degradation of pollutants (dye and pharmaceutical) in water,” Mar. 2026. <https://doi.org/10.1007/s42114-026-01696-9>
 112. M. Nanjappan, H. Rajagopalan, V. Pandurangan, and P. Elaiyaraja, “Structural, optical and magnetic properties of CoFe₂O₄ coupled with Sulfur-doped g-C₃N₄ for enhanced visible light-driven photocatalytic antibacterial drug and industrial dye degradation applications,” May 2026. <https://doi.org/10.1007/s42247-026-01425-4>
 113. X. Liu, Y. Fang, C. Yang, G. I. Abdulrasheed, and X. Feng, “Oxygen Vacancy-Engineered pg-C₃N₄/CdS/BiOCl Ternary Heterojunction Photocatalysts for Enhanced Visible-Light-Driven Degradation of Tetracycline,” Jan. 2026. <https://doi.org/10.2139/ssrn.6517200>
 114. R. Zhang and K. Zeng, “A novel flower-like dual Z-scheme BiSI/Bi₂WO₆/g-C₃N₄ photocatalyst has excellent photocatalytic activity for the degradation of organic pollutants under visible light,” Mar. 2021. <https://doi.org/10.1016/j.diamond.2021.108343>
 115. M. Alhaddad and M. S. Amin, “Removal of ciprofloxacin applying Pt@BiVO₄-g-C₃N₄ nanocomposite under visible light,” Feb. 2022. <https://doi.org/10.1016/j.optmat.2022.111976>
 116. G. Rana, R. Verma, E. A. Alabdulkarem, S. K. Rao, and K.-Y. A. Lin, “Z-Scheme CoFe₂O₄/g-C₃N₄/MWCNT catalyst for the degradation of organic pollutants: electrochemical evaluation and HPLC analysis of the intermediates,” Jun. 2026. <https://doi.org/10.1039/d6ra02055k>
 117. Y. Tang, X. Cheng, J. Wang, M. Gao, and X. Deng, “Construction of g-C₃N₄/NCQDs/FeTiO₃ heterojunction and its visible light-driven degradation performance study on methylene blue,” Jun. 2025. <https://doi.org/10.1007/s10854-025-15060-y>
 118. R. Kumari and R. Kumar, “Enhanced photocatalytic performance of 2D/3D g-C₃N₄/MoS₂ heterojunction for water remediation of real-world pollutants,” Jul. 2025. <https://doi.org/10.1063/5.0266899>
 119. P. Zhu, S. Zhang, R. Liu, D. Luo, and H. Yao, “Investigation of an enhanced Z-scheme magnetic recyclable BiVO₄/GO/CoFe₂O₄ photocatalyst with visible-light-driven for highly efficient degradation of antibiotics,” Jul. 2022. <https://doi.org/10.1016/j.jssc.2022.123379>
 120. M. Zhang, T. Wang, C. Bian, N. Yang, and H. Qi, *et al.*, “Designing novel step-scheme heterojunction g-C₃N₄/TMCs/GO with effective charge transfer for photocatalytic degradation of organic pollutant under visible light,” Nov. 2022. <https://doi.org/10.1016/j.seppur.2022.122736>
 121. S. Jiang, G. Zheng, F. Zhang, H. Yu, and Y. Cai, *et al.*, “CTAB-regulated Bi/Bi₂WO₆ heterojunction with effectively enhanced visible light photocatalytic degradation of pollutants,” May 2026. <https://doi.org/10.1007/s10854-026-17487-3>
 122. K. Wang, X. Su, Z. Zhou, L. Hu, and H. Li, *et al.*, “Dual-Effect of S-Scheme Heterojunction and

- CQDs Strengthens the Charge Separation and Transfer in CQDs-g-C₃N₄/TiO₂ Photocatalysts Toward Efficient Tetracycline Degradation,” Jan. 2026. <https://doi.org/10.3390/nano16030181>
123. K. Milošević, D. Lončarević, T. Mudrinić, M. Kalagasidis Krušić, and J. Dostanić, *et al.*, “Mechanistic insights into the simultaneous visible-light induced photodegradation of organic pollutants by g-C₃N₄/titanate heterojunction,” Jan. 2023. <https://doi.org/10.1007/s11051-023-05673-x>
 124. Chowdhury, S. Balu, K.-W. Lan, L. W.-C. Lee, and T. C.-K. Yang, “Synergistic Effect of BiVO₄/P-g-C₃N₄ Heterojunction with Enhanced Optoelectronic Properties on Synthetic Colorants under Visible Light,” Jun. 2023. <https://doi.org/10.3390/colorants2020019>
 125. X. Zheng, X. Zhang, Y. Cai, S. Zhao, and S. Wang, “Efficient degradation of bisphenol A with MoS₂/BiVO₄ hetero-nanoflower as a heterogenous peroxymonosulfate activator under visible-light irradiation,” Dec. 2021. <https://doi.org/10.1016/j.chemosphere.2021.133158>
 126. M. Ismael and M. Wark, “Photocatalytic activity of CoFe₂O₄/g-C₃N₄ nanocomposite toward degradation of different organic pollutants and their inactivity toward hydrogen production: The role of the conduction band position,” Jan. 2022. <https://doi.org/10.1016/j.flatc.2022.100337>
 127. V. Rathi, A. Panneerselvam, and R. Sathiyapriya, *et al.*, “A novel hydrothermal induced BiVO₄/g-C₃N₄ heterojunctions visible-light photocatalyst for effective elimination of aqueous organic pollutants,” Jul. 2020. <https://doi.org/10.1016/j.vacuum.2020.109458>
 128. P. Mohan, S. Mallapur, C. P. Prathibha, B. M. Rajesh, and S. Kandaiah, “Integrating the bicrystalline monoclinic-tetragonal BiVO₄ with g-C₃N₄ to form S-scheme heterojunction for bromocresol green dye degradation under visible light,” Jan. 2026. <https://doi.org/10.1007/s10854-025-16555-4>
 129. Y. Qin, H. Li, J. Lu, Y. Ding, and C. Ma, “Fabrication of Bi₂WO₆/In₂O₃ photocatalysts with efficient photocatalytic performance for the degradation of organic pollutants: Insight into the role of oxygen vacancy and heterojunction,” May 2020. <https://doi.org/10.1016/j.appt.2020.05.014>
 130. K. Perumal, P. Krishnan, B. R., K. Anandan, and A. C., “Dual Z-Scheme g-C₃N₄/MoS₂/ZnO Photocatalyst for Efficient Visible-Light Antibiotic Degradation,” Jun. 2026. <https://doi.org/10.1007/s42250-026-01738-1>
 131. X. Li, T. Chen, Y. Qiu, Z. Zhu, and H. Zhang, “Magnetic dual Z-scheme g-C₃N₄/BiVO₄/CuFe₂O₄ heterojunction as an efficient visible-light-driven peroxymonosulfate activator for levofloxacin degradation,” Oct. 2022. <https://doi.org/10.1016/j.cej.2022.139659>
 132. K. Shekhawat, V. K. Mishra, S. Pooniya, A. Bagaria, and D. Bhalothia, “Rapid visible-light-driven Rose Bengal dye degradation over a hydrothermally assembled g-C₃N₄-MXene composite,” Jun. 2026. <https://doi.org/10.1007/s42452-026-08945-y>
 133. P. Zhu, D. Luo, M. Liu, M. Duan, and J. Lin, “Flower-globular BiOI/BiVO₄/g-C₃N₄ with a dual Z-scheme heterojunction for highly efficient degradation of antibiotics under visible light,” Jun. 2022. <https://doi.org/10.1016/j.seppur.2022.121503>
 134. T.-Y. Huang, P. Naruphontjirakul, J.-Y. Lin, and W.-T. Su, “Enhanced Visible-Light-Driven Degradation of Benzophenone-3 over g-C₃N₄/WO₃ Z-Scheme Heterojunction Nanocomposites,” Jan. 2026. <https://doi.org/10.2139/ssrn.6845403>
 135. H. H. Haitosa, O. A. Zelekew, Y.-N. Wu, and D. M. Kabtamu, “Synergistic Mg Doping and Phase Engineering of MoS₂/g-C₃N₄ Catalysts: Boosting Visible-Light-Driven Photo-Fenton Pollutant Remediation,” Oct. 2025.
 136. Sharma, S. K. Kanth, S. Xu, N. Han, and Z. Lei, “Visible light driven g-C₃N₄/Bi₄NbO₈X (X=Cl, Br) heterojunction photocatalyst for the degradation of organic pollutants,” Nov. 2021. <https://doi.org/10.1016/j.jallcom.2021.162576>
 137. X. Zhang, Y. Gong, X. Dong, X. Zhang, and C. Ma, “Fabrication and efficient visible light-induced photocatalytic activity of Bi₂WO₆/BiVO₄ heterojunction,” Oct. 2012. <https://doi.org/10.1016/j.matchemphys.2012.07.013>
 138. G. Zhao, J. Ding, F. Zhou, X. Chen, L. Wei, *et al.*, “Construction of a visible-light-driven magnetic dual Z-scheme BiVO₄/g-C₃N₄/NiFe₂O₄ photocatalyst for effective removal of ofloxacin: Mechanisms and degradation pathway,” Aug. 2020. <https://doi.org/10.1016/j.cej.2020.126704>
 139. Y. Xu, B. Hu, J. Liu, K. Tao, and R. Wang, “Visible light-activated degradation of microcystin-LR by ultrathin g-C₃N₄ nanosheets-based heterojunction photocatalyst,” Sep. 2019. <https://doi.org/10.1111/jace.16773>
 140. Maosheng Tian, Chenyan Hu, Junxia Yu, and Lianguo Chen, “Carbon quantum dots (CQDs) mediated Z-scheme g-C₃N₄-CQDs/BiVO₄ heterojunction with enhanced visible light photocatalytic degradation of Paraben,” Mar. 2023. <https://doi.org/10.1016/j.chemosphere.2023.138248>
 141. Dang Van Do, Cham Thanh Le, Xoan Thi Nguyen, Son Thanh Le, and Khai Manh Nguyen, “Photodegradation of diclofenac in aqueous media via a HO[•] radical pathway using CeO₂/g-C₃N₄ heterojunction under visible light: experimental and computational insights,” Oct. 2025. <https://doi.org/10.1039/D5RA06295K>
 142. Naveed Ahmad, Chung Feng Jaffrey Kuo, and Mujahid Mustaqeem, “Synthesis of novel CuNb₂O₆/g-C₃N₄ binary photocatalyst towards efficient visible light reduction of Cr (VI) and dyes degradation for environmental remediation,” Mar.

2022.
<https://doi.org/10.1016/j.chemosphere.2022.134153>
143. Yun-hui Si, Wei-min Chen, Shao-ke Shang, Yu Xia, and Xie-rong Zeng, "g-C₃N₄/Pt/BiVO₄ nanocomposites for highly efficient visible-light photocatalytic removal of contaminants and hydrogen generation," Jan. 2020.
<https://doi.org/10.1088/1361-6528/ab5bc5>
 144. N. Ahmad, M.I. Nabeel, S.J. Ali, B. Fatima, H.N. Rashid, M. Najam-ul-Haq, S.G. Musharraf, D. Hussain, hierarchically grown CeO₂/GO on nylon filter with enhanced hydrophilicity and permeation flux for oil-water separation, *Sustainable Materials and Technologies* 37 (2023) e00698.
<https://doi.org/https://doi.org/10.1016/j.susmat.2023.e00698>
 145. Mazen R. Alrahili, Mohamed Abdel Rafea, Magdi E. A. Zaki, M. Khairy, and Mohamed R. El-Aassar, "Rationally designed In-CeO₂/g-C₃N₄ S-scheme heterojunction photocatalyst with tuned redox ability for the photocatalytic degradation of pharmaceutical contaminants," Dec. 2025.
<https://doi.org/10.1039/D5RA07023F>
 146. Garima Rana, Pooja Dhiman, Amit Kumar, Elmuez A. Dawi, and Gaurav Sharma, "Visible-Light Driven Z-scheme g-C₃N₄/Fe-MOF Photocatalyst for Degradation of Organic Pollutants," Feb. 2024.
<https://doi.org/10.1007/s10904-024-03005-7>
 147. Qasim, M., Manzoor, S., M. I. Nabeel, Ullah, Q., Sair, Y.Z., Khomphet, T., Joseph, C.G., Raza, A., Suazo-Hernández, J. and Gulzar, T., 2026. Waste-Derived Nanocomposites as Dual-Function Materials for Water and Energy Sustainability. *Frontiers in Sustainability*, 7, p.1777462.(2026)
<http://doi.org/10.3389/frsus.2026.1777462>
 148. N.M. Khan, A. Moied, S. Kiran, T. Gulzar, I. Pervez, R. Shahid, M. I. Nabeel, A. Ali, Prunus armeniaca assisted green synthesis of Fe₂O₃ /NiO nanohybrids using unripened fruit extract for remediation of Acid Orange 7 Dye. *A Sustainable Environmental Cleaner Approach. Waste and Biomass Valorization*, 2024.
<https://doi.org/10.1007/s12649-024-02738-3>
 149. Xiaodan Miao, Xiaowen Liu, Yuanfan Wang, and Pei Chen, "Enhanced photocatalytic degradation properties of a g-C₃N₄/BiVO₄ heterostructure system induced by surface and interface heterojunctions," Mar. 2024.
<https://doi.org/10.1007/s10853-024-09548-x>
 150. Qin Lisiyuan he, Liang Wang, Mengxin Zhao, and Tao Guo, "A novel Z-scheme heterojunction g-C₃N₄/g-C₃N₄/Pr₆O₁₁ for efficient visible-light photocatalytic degradation of sulfonamide," Feb. 2024. <https://doi.org/10.1002/aoc.7344>
 151. N. Ahmad, S. Rasheed, M.I. Nabeel, W. Ahmad, A. Mohyuddin, S.G. Musharraf, M. Najam-ul-Haq, D. Hussain, Stearic Acid and CeO₂ Nanoparticles Co-Functionalized Cotton Fabric with Enhanced UV-Block, Self-Cleaning, Water-Repellent, and Antibacterial Properties, *Langmuir* 39(33) (2023) 11571-11581. <https://doi.org/10.1021/ac 002>
 152. Yichen Bai, Wei Mao, Yuqing Wu, Yunhang Gao, and Tianye Wang, "Synthesis of Novel Ternary Heterojunctions via Bi₂WO₆ coupling with CuS and g-C₃N₄ for the Highly Efficient Visible-light Photodegradation of Ciprofloxacin in Wastewater," Sep. 2020.
<https://doi.org/10.1016/j.colsurfa.2020.125481>
 153. Arif, S., Rasheed, S., Nabeel, M. I., Ahmad, W., Riaz, M. T., Musharraf, S. G., & Hussain, D. (2025). Enhanced Photocatalytic Activity of Sulfur-Nitrogen Co-Doped TiO₂ Nanoparticles Synthesized using Dactylorhiza hatagirea Root Extract. *ChemistrySelect*, 10(34), e01568
<https://doi.org/10.1002/slct.202501568>
 154. G. Palanisamy, Nora Hamad Al-Shaalan, K. Bhuvaneswari, G. Bharathi, and G. Bharath, "An efficient and magnetically recoverable g-C₃N₄/ZnS/CoFe₂O₄ nanocomposite for sustainable photodegradation of organic dye under UV-visible light illumination," Jun. 2021.
<https://doi.org/10.1016/j.envres.2021.111429>
 155. Joseph, C.G., Anisuzzaman, S.M., Masjedin, N.N.D., Masjedin, D., Moktar, A.S., Nasir, W., M. I. Nabeel, Tahir, N. and Bade, A., 2026. Removal of residual antibiotics from aquaculture wastewater using ozonation and sonochemical treatment processes: a comprehensive review. *Chemical Papers*, pp.1-34. (2026),
<http://doi.org/10.1007/s11696-026-04687-8>
 156. N. Ahmad, T. Ali, T., Nabeel, K. Ahmed, H. Baggash, M. Hasnain, & D. Hussain, (2025). Facile modification of nylon filter via vacuum coating with chitosan@ MCM-41/GO for efficient oily wastewater treatment. *Journal of Materials Chemistry A*.
<https://doi.org/10.1039/D5TA02462E>
 157. Affandi, N. A., Joseph, C. G., M. I. Nabeel, Abd Majid, M. H., & Ghazali, K. Photolytic and Photocatalytic Degradation of Detergent and Surfactant Solutions by Various Light Sources *Malaysian Journal of Chemistry*, (2025), Vol. 27(6), 41-63 <https://doi.org/10.55373/mjchem.v27i6.41>
 158. Akshay Verma, Pooja Dhiman, Chin Wei Lai, Mu. Naushad, and Alberto García-Peñas, "Fabrication of visible light-driven magnetically separable Ag₃PO₄/Fe₃O₄/g-C₃N₄ photo catalyst for tetracycline degradation," Jul. 2025.
<https://doi.org/10.1007/s11051-025-06392-1>
 159. Jiajia Wang, Lin Tang, Guangming Zeng, Yani Liu, and Yaoyu Zhou, "Plasmonic Bi Metal Deposition and g-C₃N₄ coating on Bi₂WO₆ Microspheres for Efficient Visible Light Photocatalysis," Nov. 2016.
<https://doi.org/10.1021/acssuschemeng.6b02351>